

Preparation of Zinc Oxide Nanoparticles and its Cancer Treatment Effects: A Review Paper

Hemra Hamrayev¹, Kamyar Shameli^{1,*}, Mostafa Yusefi¹

¹ Department of Environment and Green Technology, Malaysia-Japan International Institute of Technology. Universiti Teknologi Malaysia, Jalan Sultan Yahya Petra, 54100 Kuala Lumpur, Malaysia

ABSTRACT

Zinc oxide nanoparticles (ZnO NPs) are one of the prominent metal oxide nanoparticles with significant applications in cancer treatment. Various methods of synthesis have been adopted in the production of ZnO NPs to meet its high demand. The environmental implications and economic challenges attached to most of the means of ZnO NPs synthesis have resulted in the quest for other alternatives with environmental and economic benefits. Recently in nanotechnology research, synthesis of nanoparticle from green chemistry pathways has been preferred due to its natural biological reduction property which reduces the utilization and exposure of toxic chemical to the environment when compare to physical and chemical methods. Among the different inorganic nanoparticles, ZnO NPs attracts more attention due to its, large bandwidth, high excitation binding energy, simplicity, easy fabrication, bio-safe, non-toxic, biocompatible, eco and environmentally friendly. Zinc oxide nanoparticle is readily soluble in biological fluids and tends to aggregate easily under different physiological condition. But physicochemical properties of the nanoparticle have an impact in the bioavailability. This review described the summary of the recent advances in the synthesis, characterization techniques, and applications of biosynthesized ZnO NPS in cancer treatment.

Keywords:

Zinc oxide nanoparticles, synthesis methods, cancer treatment

Received: 8 Jun. 2020

Revised: 14 Jul. 2020

Accepted: 22 Sep. 2020

Published: 4 Oct. 2020

1. Introduction

Recently, nanotechnology has become the center of research interest for its potential to manufacture and control materials on the scale of nano-size [1][2]. It deals with materials having a nanoscale dimension in the range of 1 to 100 nm [3][4]. Nanomaterials display distinctive property and features having extremely small size and larger surface area which makes them highly valued than their bulk materials itself [5][6]. Metal oxide nanoparticles have received substantial research attention due to their low production costs, stability and extraordinary magnetic, electrical, optical and catalytic properties for a wide range of applications including medical [7][8][9].

Zinc oxide nanoparticles (ZnO-NPs) is interesting due to their unique properties including high photosensitivity physical and chemical stability, high thermal conductivity, non-toxicity, large excitation binding energy (60 meV) as well as wide band gap (3.37 eV) [10][11]. It has numerous applications in various areas such as pharmaceuticals, agrochemicals, perfumes, dyes, petroleum,

* Corresponding author.

E-mail address: kamyarshameli@gmail.com

and biology due to its low toxicity in vitro and in vivo. Next to these applications, ZnO-NPs are likewise used in biomedical applications including anticancer [12], antibacterial [13], antioxidant [14], anti-inflammatory [15], drug delivery [16] and antifungal [17] uses due to its high biocompatibility, and stability under harsh environmental conditions. Numerous available researches reported on the preparation of zinc oxide nanoparticles (ZnO-NPs) using various methodological approaches like solvothermal and hydrothermal synthesis [18], precipitation [19], polymerization method [20], laser ablation [21], microwave irradiation [22], wet chemical method [23], a photochemical method [24], sonochemical [25], and sol-gel methods [26]. Yet, physical and chemical methods suffer various downsides such as usage of hazardous and toxic chemicals, high energy demand, and costly high which limits their biomedical applications. Therefore, alternative green synthesis of ZnO-NPs to conventional methods has emerged which is cost-effective, less toxic, eco-friendly, biocompatible, and highly efficient using biopolymers [27][28].

2. Preparation Methods of Zinc Oxide Nanoparticles.

Zinc oxide nanoparticles can be synthesized using a variety of methods such as chemical, physical, and biological. Physical and chemical methods consist of precipitation, wet chemical, microemulsion, chemical reduction, sonochemical method, solvothermal method, pulsed laser deposition, spray pyrolysis, vapor transport, and condensation, sputtering, sol-gel, gamma irradiation, microemulsion, microwave-assisted irradiation, co-precipitation, a hydrothermal technique [29][30]. Yet, green synthesis of zinc oxide nanoparticles has many advantages on chemical and physical methods. Some of the preparation methods will be discussed here.

2.1 Microwave Assisted Irradiation

Microwave irradiation synthesis has been popularly used in the fabrication of zinc oxide nanoparticles due to its advantages over conventional methods. Using this method enhances higher yields, reaction rates, improved purity, ease of workup after the reaction in an eco-friendly manner than the traditional methods. To prepare ZnO nanoparticles 200 mL aqueous solution of 25mM Zn(NO₃)₂ was prepared [31]. Later aqueous solution of ammonium hydroxide (28% NH₃) was added until the pH reaches 12 [31]. Next ZnO-seeded paper of 4 cm by 5cm was soaked in the prepared zinc nitrate solution and placed inside the microwave oven (General Electric Company, JE12340WPSL, China) set at 180W and 450W. Lastly, the substrate was removed from the growth solution, rinsed with deionized water several times, and dried at 90 °C for 6 hours. Microwave synthesis has the ability to heat either the solvent or the precursor molecules for nanomaterials preparation selectively.

2.2 Sol-gel technique

Sol-gel synthesis is introduced by Spanhel and Anderson in 1991, which uses a zinc precursor salt (nitrate, sulphate, chloride, etc.) where condensation and hydrolysis take place. In this method, the sol/solution was stirred until the aqueous solvent is completely removed; leaving a gel-like product. After, this solution will be exposed to thermal treatment under annealing temperatures up to 1000 °C min until it turned into fine powder form [32]. The white color ZnO-NPs powder was then stored at room temperature at about 25 °C for future experiments [33]. It is an easy way to prepare various sizes and to have relatively higher purity. Most of the studies reported the synthesis of ZnO-NPs in biopolymer in order to increase the stability of the product. Here, a possible schematic illustration of the synthesis of ZnO-NPs in biopolymer is drawn.

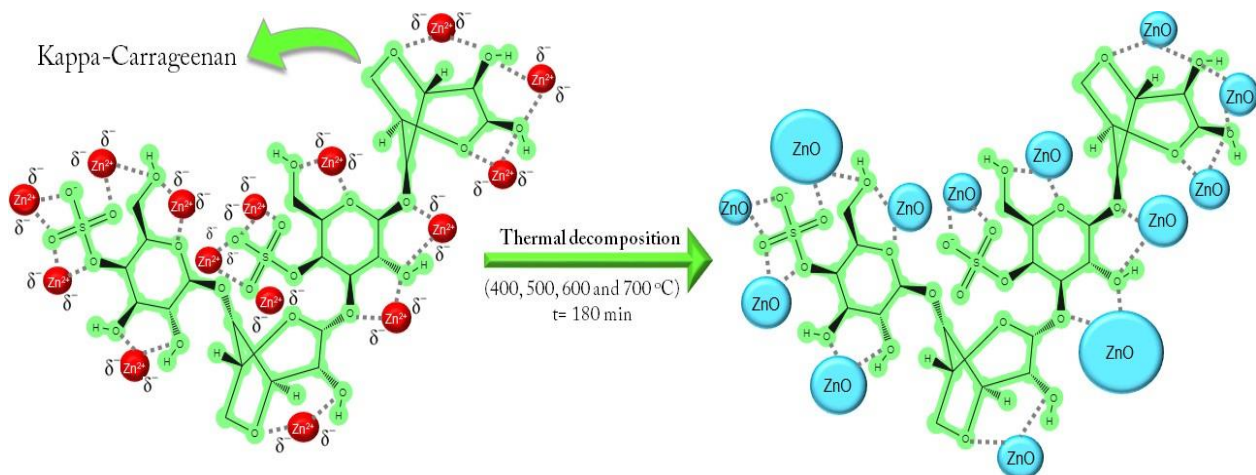


Fig. 1. Schematic illustration of Zn²⁺ ions with the main compounds found in carrageenan to synthesize ZnO-NPs

2.3 Microemulsion

This method is one of the ideal techniques for the fabrication of inorganic nanoparticles, yet the mechanism of nanoparticle formation in the micro-emulsion is a complex process to understand. Some researchers have introduced a mechanism for nanoparticle synthesis in microemulsions in water-water or water-oil. Microemulsion material consists of reactants mixed together, exchange of reactants occurs during the collision of nano-droplets resulting in the nucleation growth and formation of final nanoparticles surrounded by water or stabilized by surfactants. For instance, microemulsions were prepared in the ratio of 1:1 mixing Tween 80 to form an organic phase [34]. Then, the 0.5 M aqueous solution of zinc acetate was added as a zinc precursor and mixed together under magnetic stirring at 1200 rpm for 5 min and stored for 24 hr at room temperature [34]. The 1.0 M aqueous solution of sodium hydroxide, NaOH (97.0% purity) added to the above solution as a precipitant agent. The mixtures were kept at 60 °C and stirred at 1200 rpm for 5 min. Afterward, the mixtures were consecutively washed by centrifugation at 7500 rpm in water, acetone, and hexane, in order to separate the oil and surfactant residues from the precipitate, as well as water-soluble salts resultants of the reaction. Finally, ZnO-NPs were obtained after calcination at 800 °C for 2 h.

2.4 Laser Ablation

The pulsed laser method is another process of synthesizing ZnO-NPs by removing material from a liquid solution irradiating it with a laser beam. The material is heated by the absorbed laser energy where it evaporates or sublimates. Usually, the material is converted into plasma at high laser flux. For example, to produce nanoparticles zinc metal is mixed with distilled water in a beaker where the water level is 5 mm above the metal target, approximately 95 ml of water. ZnO nanoparticle solution was obtained by the irradiation of zinc metal with Ytterbium fiber laser (IPG Laser: YLP-1-100-20-20-HC) which operated with the following parameters at 1064 nm wavelength, 7 ns pulse duration, 20 Hz, and 150 ml [35]. The initial powders formed by ablation were additionally heat treated in a SNOL 6.7/1300 muffle furnace (Litva) in atmospheric air at 300 and 500°C for 4 h at a heating rate of 10°C/min to produce ZnO nanoparticles [35].

2.5 Hydrothermal Synthesis

This method has been generally appreciated, accumulating consideration from researchers and technologists from various disciplines. It was first utilized by British geologist Roderick Murchison (1792–1871) to portray the activity of water at raised temperature and pressure in achieving changes in the earth's crust prompting the production of rocks and minerals. The hydrothermal technique has been successful for the synthesis of significant solids, for example, microporous crystals, chemical sensing oxides, superionic conductors, complex oxide ceramic and fluorides, electronically conducting solids, magnetic materials, and luminescence phosphors. It is likewise a route to exceptional dense material, including nano-meter particles, gels, distinguished helical and chiral structures, thin films, and especially stacking-sequence materials. For example, in order to synthesize ZnO NPs using the clove hydroalcoholic extract, different amounts of zinc nitrate (2–6 g) were added into various amounts of the obtained clove extract (10–20 mL) and placed into a laboratory autoclave set at a temperature of 121°C and a pressure of 1.5 atm for 15 min [36]. Later, the mixture solutions containing ZnO NPs were decanted into ceramic crucible cups and placed into the laboratory furnace adjusted at 350°C for 2 h to result in a pale yellow powder of ZnO NPs [36]. One of the advantageous of the hydrothermal synthesis is that it is an easy process to control the size, shape distribution, and crystallinity of the final product through adjustment of the parameters, such as reaction temperature, reaction time, solvent type, surfactant type, and precursor type. Moreover, most materials can be made soluble in a proper solvent by heating and pressuring the system close to its critical point.

2.6 Sonochemical Method

The sonochemical method has been studied in the synthesis of zinc oxide nanoparticles. Acoustic cavitation and chemical influences of ultrasound are two main concerns in the sonochemical method. It is another technique used in producing new materials with a complex design by high-intensity ultrasound without applying high pressure and temperature within a short period of time. The irradiation of ultrasound gives high acoustic waves and bubbles or cavities with swing bringing about the possible application of ultrasound strength effectively to produce the nanoparticles with the appropriate formation and small size. Various studies are done in the synthesis of zinc oxide nanoparticles. For example, varying amounts of ZnCl₂ (1.5 g to 18.5 g) were added into a beaker to get the total volume of 100 ml of solution [25]. The solution was sonicated for 5 min until it became a homogenous solution. Different amount of NaOH granules (3.3 g to 11.7 g) was added into the running solution [25]. For further completion of the reaction mechanism, the solution was then sonicated for various time intervals (19.7 min to 70.2 min) based on CCD under ultrasonic probe homogenizer (Bandelin Sonopuls HD 3200, Bandelin Electronic GmbH & Co. KG, Berlin, Germany, 20 kHz, 200 W, 50% efficiency). After the completion of the sonication process, the resulting white flocculates were washed five times with ethanol to remove the excess amount of trashes and impurities. The successful synthesis of zinc oxide nanoparticles is obtained after centrifugation at 4000 rpm for min.

2.7 Gamma Irradiation

Gamma irradiation is one of the favored techniques for the synthesis of the metallic nanoparticle. It is an easy, cost-effective technique and uses less hazardous precursors such as water or ethanol. Moreover, it does not require high energy temperature and limits waste. The radiolytic decrease has

been demonstrated to be a powerful tool in the fabrication of mono-sized and highly dispersed metallic clusters. The essential impacts of the collaboration of high-energy gamma photons with a solution of metal ions are the excitation and the ionization of the solvent. The effect of gamma ray irradiation has been studied on the structural and optical properties of zinc oxide nanoparticles. The SEM images displayed that the gamma irradiation of high dose lead to increase in grain size while decreased at a low dose [37]. The optical absorption spectra of ZnO are also obtained in the wavelength range 200–800 nm before and after irradiation. The band gap is increased at the high dose of gamma radiation and decreased at a low dose [36].

2.9 Co-precipitation

This method involves the simultaneous occurrence of nucleation, growth, coarsening, and/or agglomeration processes. Nucleation is a key step in the formation of a group of small particles. During the nucleation process, controlling the pH value is very significant. Because nanoparticles grow faster, makes it difficult to control the particle size while the pH value is above 10. Metals formed from aqueous solutions, through reduction from non-aqueous solutions, electrochemical reduction, and decomposition of metal-organic precursors while oxides formed from aqueous and non-aqueous solutions. A recent study showed the synthesis of ZnO NPs using the co-precipitation method. Firstly, two solutions of 0.1 M of zinc acetate hexahydrate and 0.2 M of NaOH are prepared by dissolving them in deionized water [38]. Then these two solutions into one beaker and stirred at 750 rpm for 2 h under a temperature of 60 °C [38]. Once the transparent solution became white milky, the centrifugation was applied at 4500 rpm for 2 min, and a white product precipitated. The precipitate product was then washed with de-ionized water and then with acetone. ZnO NPs in the form of powder were obtained by drying the product using the laboratory conventional oven at 75 °C for 6 h 9 [38] [39].

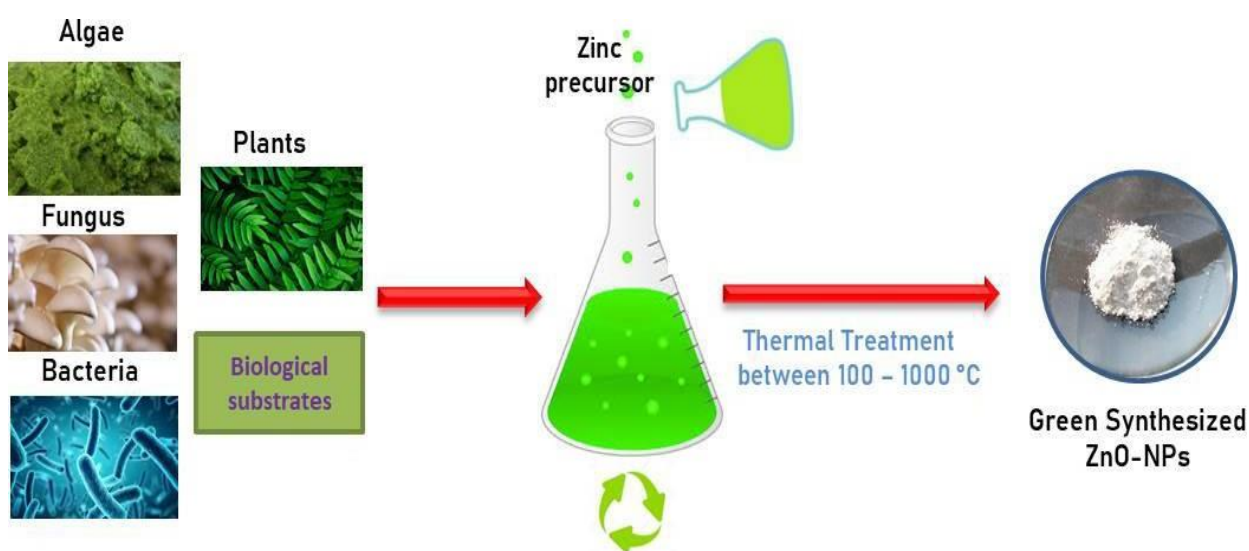


Fig. 2. Schematic illustration of green synthesis of ZnO-NPs.

2.10 Green Synthesis

Scientists choose the green synthesis of nanoparticles using plants like fruits, roots, leaves, roots and stems and microorganisms like algae, bacteria, yeast and fungi which leads to various applications [39]. Green synthesis of nanoparticles shows more catalytic activity and restricts the usage of hazardous and expensive chemicals. This green synthesis of zinc oxide nanoparticles has some benefits like a safe, cost-effective, environmentally benign, non-toxic, bio-compatible, and large-scale production is plausible [39][40].

3. Cancer Treatment Effects

Cancer statistics displayed 18.1 million new cases across the world in only 2018 alone [41]. Cancer is a state of uncontrolled malignant cell proliferation and invasion. Cancer takes lives of people mercilessly [42]. It is generally treated by radiotherapy, chemotherapy and surgery in the past for a long while. Albeit every one of these treatments appear to be successful for killing cancer cells in principle, these non-selective treatment techniques additionally present a great deal of side effects [43]. With the merge of nanotechnology, nanomaterial based nanomedicine with high biocompatibility, effective surface functionalization, drug delivery capacity, and cancer targeting has exhibited the possibility to overcome these side effects. Zn^{+2} is an essential nutrient for adults, and ZnO nanomaterials are considered to be safe in vivo. Recently, the application of ZnO as anticancer agent is of great interest in the development of biomaterials in the field of microbiology because of its stability under harsh environment conditions, high biocompatibility, fast electron transfer kinetics and longer life than organic-based disinfectants [44]. Studies have proven that ZnO is fatal to cancer cells [45]. ZnO nanoparticles can generate reactive oxygen species (ROS) when reacting with the cell membrane lipids and show higher toxicity against cancer cells in vitro [46]. As the US Food and Drug Administration (FDA) has recognized bulk ZnO as a generally recognized as safe (GRAS) substance, ZnO-NPs larger than 100 nm are considered to be relatively biocompatible, which supports their use for drug delivery [47] [48]. Various studies also have been done on the positive attitude of ZnO-NPs against cancer cells.

In terms of cancer treatment, ZnO and ZnO immersed in biopolymer have exhibited high anticancer against human breast cancer cell (MCF-7 cell line) [46], AGS gastric cancer cells [49], Human Cervical cancer (HeLa) [27], human colon cancer HCT-116 [12], colorectal cancer (HCT116) [41], human colorectal adenocarcinoma cells (Caco-2 cell line) [50]. Yet, researchers concluded that the effectiveness of biosynthesized ZnO-NPs as an anticancer agent was dose-dependent, meaning that increased concentration of ZnO-NPs increases its efficiency against cancer cells. The usage of nanoparticles in targeted drug delivery has been an exciting research opportunity for effective cancer treatment. Targeted drug delivery on cancerous cells will reduce the dosage of drugs for treatment and its other side effects. The biodegradable properties and low toxicity of ZnO NPs have increased their usage in cancer drug delivery compared to other nanoparticles.

An ideal anticancer strategy is to target both cancer cells and the tumor microenvironment due to the complexity of cancer. A study reported that zinc oxide nanoparticles (ZnO NPs) were able to target multiple cell types of cancer, including cancer cells, cancer stem cells (CSCs), and macrophages, and simultaneously perform several key functions, including inhibition of cancer proliferation, sensitization of drug-resistant cancer, prevention of cancer recurrence and metastasis, and resuscitation of cancer immune-surveillance [51]. Proposed mechanism of ZnO-NPs as a multifunctional and multi-target anticancer nanomedicine is exhibited in Figure 3.

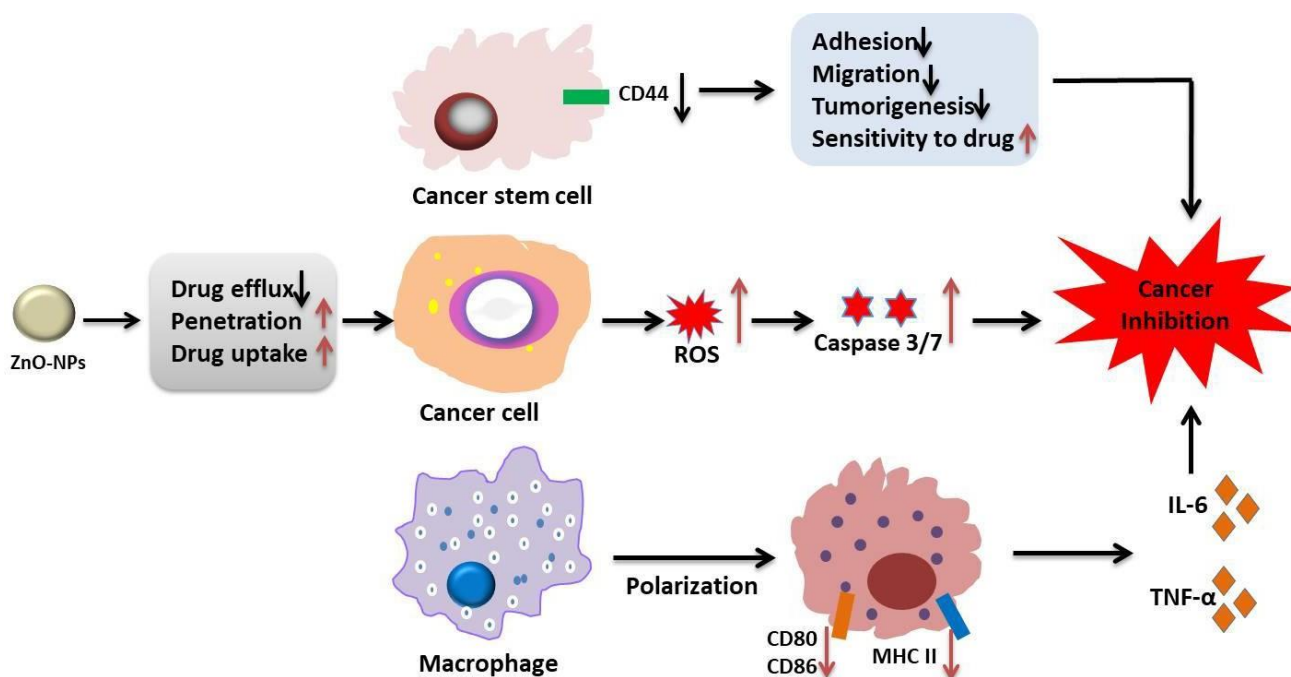


Fig. 3. Proposed mechanism of ZnO NPs that can be used as a potential multi-target and multi-functional anticancer nanomedicine.

A study also reported that ZnO-NPs could work as a pH-dependent drug carrier and displayed enhanced cellular uptake and tumor spheroid penetration [51][52]. ZnO-NPs could effectively down-regulate CD44 expression of cancer (stem-like) cells to inhibit cell adhesion, migration, and tumorigenesis, as well as sensitize drug treatment. These research results proved, ZnO NPs might have great potential to be a multi-target and multi-functional nanocarrier and nanomedicine for anticancer research.

4. Conclusions

Zinc oxide nanoparticles have gained significant interest due to their unique chemical and physical properties and are applicable to diverse areas. Various preparation methods of nanoparticles have been developed and they are suitable for the synthesis of nanoparticles in different sizes and shapes. The methods that were discussed include gamma irradiation, sol-gel, co-precipitation, sonochemical, hydrothermal, laser ablation, microemulsion, microwave-assisted irradiation, and green synthesis. Green synthesis of zinc nanoparticles has gained much importance recently due to its biocompatible and eco-friendly nature. Green sources act as both stabilizing and reducing agent for the synthesis of shape and size controlled nanoparticles. ZnO-NPs can be characterized using various tools such as XRD, UV-vis spectroscopy, FTIR, TEM and SEM for the confirmation of successfully produced ZnO-NPs. The outcome of this study will hopefully serve as a guide to anyone intending to conduct research on a similar field of interest. Moreover, the green synthesis of zinc oxide nanoparticles is greatly applicable for cancer treatment due to their non-toxicity and biocompatibility.

Acknowledgement

The authors would like to express sincere gratitude to the Universiti Teknologi Malaysia (UTM) and Malaysia-Japan International Institute of Technology (MJIT) for financial support under research university grants (Takasago Thermal Engineering Co. Ltd. grant (#4B422)).

References

- [1] A Rama Narsimha, Reddy and Srividya L. "Evaluation of in Vitro Cytotoxicity of Zinc Oxide (Zno) Nanoparticles Using Human Cell Lines." *Journal of Toxicology and Risk Assessment* 4, no. 1 (2018).
<http://dx.doi.org/10.23937/2572-4061.1510009>.
- [2] Adam, Rania E., Gallia Pozina, Magnus Willander, and Omer Nur. "Synthesis of Zno Nanoparticles by Co-Precipitation Method for Solar Driven Photodegradation of Congo Red Dye at Different Ph." *Photonics and Nanostructures - Fundamentals and Applications* 32 (2018): 11-18.
<http://dx.doi.org/10.1016/j.photonics.2018.08.005>.
- [3] Agarwal, H. and V. Shanmugam. "A Review on Anti-Inflammatory Activity of Green Synthesized Zinc Oxide Nanoparticle: Mechanism-Based Approach." *Bioorg Chem* 94 (Jan 2020): 103423.
<http://dx.doi.org/10.1016/j.bioorg.2019.103423>.
- [4] Ahmar Rauf, Mohd, Mohammad Oves, Fawad Ur Rehman, Abdur Rauf Khan, and Nazim Husain. "Bougainvillea Flower Extract Mediated Zinc Oxide's Nanomaterials for Antimicrobial and Anticancer Activity." *Biomedicine & Pharmacotherapy* 116 (2019).
<http://dx.doi.org/10.1016/j.biopha.2019.108983>.
- [5] Akintelu, Sunday Adewale and Aderonke Similoluwa Folorunso. "A Review on Green Synthesis of Zinc Oxide Nanoparticles Using Plant Extracts and Its Biomedical Applications." *BioNanoScience* 10, no. 4 (2020): 848-63.
<http://dx.doi.org/10.1007/s12668-020-00774-6>.
- [6] Aminuzzaman, Mohammad, Pei Sian Ng, Wee-Sheng Goh, Sayaka Ogawa, and Akira Watanabe. "Value-Adding to Dragon Fruit (Hylocereus Polyrhizus) Peel Biowaste: Green Synthesis of Zno Nanoparticles and Their Characterization." *Inorganic and Nano-Metal Chemistry* 49, no. 11 (2019): 401-11.
<http://dx.doi.org/10.1080/24701556.2019.1661464>.
- [7] Anvarinezhad, Mahvash, Afshin Javadi, and Hoda Jafarizadeh-Malmiri. "Green Approach in Fabrication of Photocatalytic, Antimicrobial, and Antioxidant Zinc Oxide Nanoparticles – Hydrothermal Synthesis Using Clove Hydroalcoholic Extract and Optimization of the Process." *Green Processing and Synthesis* 9, no. 1 (2020): 375-85.
<http://dx.doi.org/10.1515/gps-2020-0040>.
- [8] Arote, S. A., A. S. Pathan, Y. V. Hase, P. P. Bardapurkar, D. L. Gapale, and B. M. Palve. "Investigations on Synthesis, Characterization and Humidity Sensing Properties of Zno and Zno-Zro2 Composite Nanoparticles Prepared by Ultrasonic Assisted Wet Chemical Method." *Ultrason Sonochem* 55 (Jul 2019): 313-21.
<http://dx.doi.org/10.1016/j.ultsonch.2019.01.012>.
- [9] Yusefi, M., Shameli, K., Jumaat, A. F., Preparation and properties of Magnetic Iron Oxide Nanoparticles for Biomedical Applications: A Brief Review. *Journal of Advanced Research in Materials Science* 75, no. 1 (2020) 10-18.
<https://doi.org/10.37934/arms.75.1.1018>
- [10] Bandeira, Marina, Marcelo Giovanela, Mariana Roesch-Ely, Declan M. Devine, and Janaina da Silva Crespo. "Green Synthesis of Zinc Oxide Nanoparticles: A Review of the Synthesis Methodology and Mechanism of Formation." *Sustainable Chemistry and Pharmacy* 15 (2020).
<http://dx.doi.org/10.1016/j.scp.2020.100223>.
- [11] Costa, B. C., E. A. Rodrigues, C. K. Tokuhara, R. C. Oliveira, P. N. Lisboa-Filho, and L. A. Rocha. "Zno Nanoparticles with Different Sizes and Morphologies for Medical Implant Coatings: Synthesis and Cytotoxicity." *BioNanoScience* 8, no. 2 (2018): 587-95.
<http://dx.doi.org/10.1007/s12668-018-0514-7>.
- [12] Dhandapani, Kayal Vizhi, Devipriya Anbumani, Arumugam Dhanesh Gandhi, Purandaradas Annamalai, Bala Sundaram Muthuvenkatachalam, Purushothaman Kavitha, and Babujanarathanam Ranganathan. "Green Route for the Synthesis of Zinc Oxide Nanoparticles from Melia Azedarach Leaf Extract and Evaluation of Their Antioxidant and Antibacterial Activities." *Biocatalysis and Agricultural Biotechnology* 24 (2020).
<http://dx.doi.org/10.1016/j.bcab.2020.101517>.
- [13] Dulta, Kanika, Gözde Koşarsoy Ağçeli, Parveen Chauhan, Rohit Jasrotia, and P. K. Chauhan. "A Novel Approach of Synthesis Zinc Oxide Nanoparticles by Bergenia Ciliata Rhizome Extract: Antibacterial and Anticancer Potential." *Journal of Inorganic and Organometallic Polymers and Materials* (2020).
<http://dx.doi.org/10.1007/s10904-020-01684-6>.

- [14] Elsupikhe, R. F., K. Shameli, M. B. Ahmad, N. A. Ibrahim, and N. Zainudin. "Green Sonochemical Synthesis of Silver Nanoparticles at Varying Concentrations of Kappa-Carrageenan." *Nanoscale Res Lett* 10, no. 1 (Dec 2015): 916. <http://dx.doi.org/10.1186/s11671-015-0916-1>.
- [15] Faezah Farzaneh, Zahra Asgharpour, Fatemah Nouroozi, Sara Haghshenas. "Rapid Synthesis and Characterization of Zinc Oxide Nanoparticles with Albumen as Photodegradation of Congo Red under Microwave Irradation." (2017).
- [16] Gavrilenko, E. A., D. A. Goncharova, I. N. Lapin, M. A. Gerasimova, and V. A. Svetlichnyi. "Photocatalytic Activity of Zinc Oxide Nanoparticles Prepared by Laser Ablation in a Decomposition Reaction of Rhodamine B." *Russian Physics Journal* 63, no. 8 (2020): 1429-37. <http://dx.doi.org/10.1007/s11182-020-02188-z>.
- [17] George, D., P. U. Maheswari, and Kmms Begum. "Chitosan-Cellulose Hydrogel Conjugated with L-Histidine and Zinc Oxide Nanoparticles for Sustained Drug Delivery: Kinetics and in-Vitro Biological Studies." *Carbohydr Polym* 236 (May 15 2020): 116101. <http://dx.doi.org/10.1016/j.carbpol.2020.116101>.
- [18] Happy, A., M. Soumya, S. Venkat Kumar, S. Rajeshkumar, R. D. Sheba, T. Lakshmi, and V. Deepak Nallaswamy. "Phyto-Assisted Synthesis of Zinc Oxide Nanoparticles Using Cassia Alata and Its Antibacterial Activity against Escherichia Coli." *Biochem Biophys Rep* 17 (Mar 2019): 208-11. <http://dx.doi.org/10.1016/j.bbrep.2019.01.002>.
- [19] Herrera-Rivera, R., M. de la L. Olvera, and A. Maldonado. "Synthesis of ZnO Nanopowders by the Homogeneous Precipitation Method: Use of Taguchi's Method for Analyzing the Effect of Different Variables." *Journal of Nanomaterials* 2017 (2017): 1-9. <http://dx.doi.org/10.1155/2017/4595384>.
- [20] Isa, Eleen Dayana Mohamed, Kamyar Shameli, Nurfatehah Wahyuny Che Jusoh, and Roshasnorlyza Hazan. "Rapid Photodecolorization of Methyl Orange and Rhodamine B Using Zinc Oxide Nanoparticles Mediated by Pullulan at Different Calcination Conditions." *Journal of Nanostructure in Chemistry* (2020). <http://dx.doi.org/10.1007/s40097-020-00358-6>.
- [21] Ismail, A. M., A. A. Menazea, Hoda A. Kabary, A. E. El-Sherbiny, and A. Samy. "The Influence of Calcination Temperature on Structural and Antimicrobial Characteristics of Zinc Oxide Nanoparticles Synthesized by Sol-Gel Method." *Journal of Molecular Structure* 1196 (2019): 332-37. <http://dx.doi.org/10.1016/j.molstruc.2019.06.084>.
- [22] Ismail, AM, AA Menazea, Hoda A Kabary, AE El-Sherbiny, and A Samy. "The Influence of Calcination Temperature on Structural and Antimicrobial Characteristics of Zinc Oxide Nanoparticles Synthesized by Sol-Gel Method." *Journal of Molecular Structure* 1196 (2019): 332-37.
- [23] Karacacili, A., S. Korpayev, H. Dumanoglu, and S. Alizadeh. "Synthesis of Indole-3-Acetic Acid and Indole-3-Butyric Acid Loaded Zinc Oxide Nanoparticles: Effects on Rhizogenesis." *J Biotechnol* 303 (Sep 10 2019): 8-15. <http://dx.doi.org/10.1016/j.jbiotec.2019.07.004>.
- [24] Kirtay, Hicret, Birsal Can Omur, Ahmet Altindal, and Nergis Arsu. "One Step Facile in-Situ Photochemical Synthesis of Hollow, Doughnut-Like ZnO Nanoparticles and Their Alcohol Vapor Sensing Properties." *Materials Research Bulletin* 122 (2020). <http://dx.doi.org/10.1016/j.materresbull.2019.110661>.
- [25] Kwon, H. J., K. Shin, M. Soh, H. Chang, J. Kim, J. Lee, G. Ko, B. H. Kim, D. Kim, and T. Hyeon. "Large-Scale Synthesis and Medical Applications of Uniform-Sized Metal Oxide Nanoparticles." *Adv Mater* 30, no. 42 (Oct 2018): e1704290. <http://dx.doi.org/10.1002/adma.201704290>.
- [26] Lin, Zi, Jun Yue, Liang Liang, Biao Tang, Bin Liu, Lei Ren, Yan Li, and Lelun Jiang. "Rapid Synthesis of Metallic and Alloy Micro/Nanoparticles by Laser Ablation Towards Water." *Applied Surface Science* 504 (2020). <http://dx.doi.org/10.1016/j.apsusc.2019.144461>.
- [27] maheswari, Uma A., Lakshmana Prabu S, and Purat chikody A. "Biosynthesis of Zinc Oxide Nanoparticle: A Review on Greener Approach." *MOJ Bioequivalence & Bioavailability* 5, no. 3 (2018). <http://dx.doi.org/10.15406/mojbb.2018.05.00096>.
- [28] Majeed, Shahnaz, Mohammed Danish, Muhammad Hisyamuddin Bin Ismail, Mohmmmed Tahir Ansari, and Mohamad Nasir Mohamad Ibrahim. "Anticancer and Apoptotic Activity of Biologically Synthesized Zinc Oxide Nanoparticles against Human Colon Cancer Hct-116 Cell Line- in Vitro Study." *Sustainable Chemistry and Pharmacy* 14 (2019). <http://dx.doi.org/10.1016/j.scp.2019.100179>.
- [29] Mansour, Shehab, Ashraf Farha, and Mohamed Kotkata. "Synthesis and Study of ZnO Nanoparticles by Polymer Pyrolysis Route Using Two Different Polymerization Initiators." *International Journal of Applied Ceramic Technology* 14, no. 6 (2017): 1213-21.

- <http://dx.doi.org/10.1111/ijac.12751>.
- [30] Miri, Abdolhossien, Nafiseh Mahdinejad, Omolbanin Ebrahimi, Mehrdad Khatami, and Mina Sarani. "Zinc Oxide Nanoparticles: Biosynthesis, Characterization, Antifungal and Cytotoxic Activity." *Materials Science and Engineering: C* 104 (2019).
<http://dx.doi.org/10.1016/j.msec.2019.109981>.
- [31] Mishra, P. K., H. Mishra, A. Ekielski, S. Talegaonkar, and B. Vaidya. "Zinc Oxide Nanoparticles: A Promising Nanomaterial for Biomedical Applications." *Drug Discov Today* 22, no. 12 (Dec 2017): 1825-34.
<http://dx.doi.org/10.1016/j.drudis.2017.08.006>.
- [32] Mohamad Sukri, Siti Nur Amalina, Kamyar Shameli, Magdelyn Mei-Theng Wong, Sin-Yeang Teow, Jactty Chew, and Nur Afini Ismail. "Cytotoxicity and Antibacterial Activities of Plant-Mediated Synthesized Zinc Oxide (Zno) Nanoparticles Using Punica Granatum (Pomegranate) Fruit Peels Extract." *Journal of Molecular Structure* 1189 (2019): 57-65.
<http://dx.doi.org/10.1016/j.molstruc.2019.04.026>.
- [33] Mohamed Isa, E. D., N. W. Che Jusoh, R. Hazan, and K. Shameli. "Pullulan Mediated Zinc Oxide Microparticles: Effect of Synthesis Temperature." *IOP Conference Series: Materials Science and Engineering* 808 (2020).
<http://dx.doi.org/10.1088/1757-899x/808/1/012032>.
- [34] Nguyen, N. H. A., V. V. T. Padil, V. I. Slaveykova, M. Cernik, and A. Sevcu. "Green Synthesis of Metal and Metal Oxide Nanoparticles and Their Effect on the Unicellular Alga Chlamydomonas Reinhardtii." *Nanoscale Res Lett* 13, no. 1 (May 23 2018): 159.
<http://dx.doi.org/10.1186/s11671-018-2575-5>.
- [35] Noman, M. T., M. Petru, J. Militky, M. Azeem, and M. A. Ashraf. "One-Pot Sonochemical Synthesis of Zno Nanoparticles for Photocatalytic Applications, Modelling and Optimization." *Materials (Basel)* 13, no. 1 (Dec 18 2019).
<http://dx.doi.org/10.3390/ma13010014>.
- [36] Pineda-Reyes, Ana M. and M. de la L. Olvera. "Synthesis of Zno Nanoparticles from Water-in-Oil (W/O) Microemulsions." *Materials Chemistry and Physics* 203 (2018): 141-47.
<http://dx.doi.org/10.1016/j.matchemphys.2017.09.054>.
- [37] Qindeel, Rabia. "Effect of Gamma Radiation on Morphological & Optical Properties of Zno Nanopowder." *Results in Physics* 7 (2017): 807-09.
<http://dx.doi.org/10.1016/j.rinp.2017.02.003>.
- [38] Rahimi Kalateh Shah Mohammad, Ghasem, Masoud Homayouni Tabrizi, Touran Ardalani, Soheyla Yadamani, and Elham Safavi. "Green Synthesis of Zinc Oxide Nanoparticles and Evaluation of Anti-Angiogenesis, Anti-Inflammatory and Cytotoxicity Properties." *Journal of Biosciences* 44, no. 2 (2019).
<http://dx.doi.org/10.1007/s12038-019-9845-y>.
- [39] Rajan, Murugan, Allen Joseph Anthuvan, Kasipandi Muniyandi, Naveen Kumar Kalagatur, Saravanan Shanmugam, Saikumar Sathyanarayanan, Viswanathan Chinnuswamy, Parimelazhagan Thangaraj, and Narendra Narain. "Comparative Study of Biological (Phoenix Loureiroi Fruit) and Chemical Synthesis of Chitosan-Encapsulated Zinc Oxide Nanoparticles and Their Biological Properties." *Arabian Journal for Science and Engineering* 45, no. 1 (2019): 15-28.
<http://dx.doi.org/10.1007/s13369-019-04174-1>.
- [40] Saberona, Saberina I., Monet Concepcion Maguyon-Debras, Maria Victoria P. Migo, Marvin U. Herrera, and Ronniel D. Manalo. "Microwave-Assisted Synthesis of Zinc Oxide Nanoparticles on Paper." *Key Engineering Materials* 775 (2018): 163-68.
<http://dx.doi.org/10.4028/www.scientific.net/KEM.775.163>.
- [41] Sharmila, Govindasamy, Marimuthu Thirumarimurugan, and Chandrasekaran Muthukumar. "Green Synthesis of Zno Nanoparticles Using Tecoma Castanifolia Leaf Extract: Characterization and Evaluation of Its Antioxidant, Bactericidal and Anticancer Activities." *Microchemical Journal* 145 (2019): 578-87.
<http://dx.doi.org/10.1016/j.microc.2018.11.022>.
- [42] Taghavi Fardood, Saeid, Ali Ramazani, Sajjad Moradi, and Pegah Azimzadeh Asiabi. "Green Synthesis of Zinc Oxide Nanoparticles Using Arabic Gum and Photocatalytic Degradation of Direct Blue 129 Dye under Visible Light." *Journal of Materials Science: Materials in Electronics* 28, no. 18 (2017): 13596-601.
<http://dx.doi.org/10.1007/s10854-017-7199-5>.
- [43] Tang, Q., H. Xia, W. Liang, X. Huo, and X. Wei. "Synthesis and Characterization of Zinc Oxide Nanoparticles from Morus Nigra and Its Anticancer Activity of Ags Gastric Cancer Cells." *J Photochem Photobiol B* 202 (Jan 2020): 111698.
<http://dx.doi.org/10.1016/j.jphotobiol.2019.111698>.

- [44] Vijayakumar, S., K. Saravanakumar, B. Malaikozhundan, M. Divya, B. Vaseeharan, E. F. Duran-Lara, and M. H. Wang. "Biopolymer K-Carrageenan Wrapped ZnO Nanoparticles as Drug Delivery Vehicles for Anti Mrsa Therapy." *Int J Biol Macromol* 144 (Feb 1 2020): 9-18.
<http://dx.doi.org/10.1016/j.ijbiomac.2019.12.030>.
- [45] Vijayakumar, S., B. Vaseeharan, B. Malaikozhundan, and M. Shobiya. "Laurus Nobilis Leaf Extract Mediated Green Synthesis of ZnO Nanoparticles: Characterization and Biomedical Applications." *Biomed Pharmacother* 84 (Dec 2016): 1213-22.
<http://dx.doi.org/10.1016/j.biopha.2016.10.038>.
- [46] Wang, J., J. S. Lee, D. Kim, and L. Zhu. "Exploration of Zinc Oxide Nanoparticles as a Multitarget and Multifunctional Anticancer Nanomedicine." *ACS Appl Mater Interfaces* 9, no. 46 (Nov 22 2017): 39971-84.
<http://dx.doi.org/10.1021/acsami.7b11219>.
- [47] Wu, Dudu, Zhi Chen, Kangrong Cai, Dongling Zhuo, Jiayi Chen, and Bin Jiang. "Investigation into the Antibacterial Activity of Monodisperse Bsa-Conjugated Zinc Oxide Nanoparticles." *Current Applied Physics* 14, no. 11 (2014): 1470-75.
<http://dx.doi.org/10.1016/j.cap.2014.08.015>.
- [48] Wu, H. and J. Zhang. "Chitosan-Based Zinc Oxide Nanoparticle for Enhanced Anticancer Effect in Cervical Cancer: A Physicochemical and Biological Perspective." *Saudi Pharm J* 26, no. 2 (Feb 2018): 205-10.
<http://dx.doi.org/10.1016/j.jsps.2017.12.010>.
- [49] Yadollahi, M., S. Farhoudian, S. Barkhordari, I. Gholamali, H. Farhadnejad, and H. Motasadizadeh. "Facile Synthesis of Chitosan/ZnO Bio-Nanocomposite Hydrogel Beads as Drug Delivery Systems." *Int J Biol Macromol* 82 (Jan 2016): 273-8.
<http://dx.doi.org/10.1016/j.ijbiomac.2015.09.064>.
- [50] Yusefi, M., K. Shameli, H. Jahangirian, S. Y. Teow, H. Umakoshi, B. Saleh, R. Rafiee-Moghaddam, and T. J. Webster. "The Potential Anticancer Activity of 5-Fluorouracil Loaded in Cellulose Fibers Isolated from Rice Straw." *Int J Nanomedicine* 15 (2020): 5417-32.
<http://dx.doi.org/10.2147/IJN.S250047>.
- [51] Yusefi, Mostafa, Kamyar Shameli, Roshafima Rasit Ali, Siew-Wai Pang, and Sin-Yeang Teow. "Evaluating Anticancer Activity of Plant-Mediated Synthesized Iron Oxide Nanoparticles Using Punica Granatum Fruit Peel Extract." *Journal of Molecular Structure* 1204 (2020): 127539.
- [52] Zare, Mina, K. Namratha, M. S. Thakur, and K. Byrappa. "Biocompatibility Assessment and Photocatalytic Activity of Bio-Hydrothermal Synthesis of ZnO Nanoparticles by Thymus Vulgaris Leaf Extract." *Materials Research Bulletin* 109 (2019): 49-59.
<http://dx.doi.org/10.1016/j.materresbull.2018.09.025>.