

Influence of Molybdenum Disulphide (MoS_2) Nanoparticles Loading in Treated Used Palm Oil Bio-lubricant on Surface Roughness during Turning of AISI420

Muhamad Azwar Azhari¹, Nor Hasrul Akhmal Ngadiman^{1,*}, Noordin Mohd Yusof¹, Ani Idris², Norazlianie Sazali³

¹ Department of Material, Manufacturing and Industrial Engineering, Faculty of Mechanical Engineering, Universiti Teknologi Malaysia, 81310 Skudai, Johor, Malaysia

² Department of Bioprocess Engineering, Faculty of Chemical Engineering, Universiti Teknologi Malaysia, 81310 Skudai, Johor, Malaysia

³ Faculty of Manufacturing and Mechatronic Engineering Technology, Universiti Malaysia Pahang Al-Sultan Abdullah, 26600 Pekan, Pahang, Malaysia

ARTICLE INFO

Article history:

Received 5 September 2023

Received in revised form 1 November 2023

Accepted 5 December 2023

Available online 29 December 2023

Keywords:

Bio-lubricant; Zinc

Dialkyldithiophosphate; MoS_2

nanoparticles; AISI420 cutting

ABSTRACT

The environmental impact and non-biodegradability of petroleum-based lubricants has caused some researchers to shift the formulation of lubricant formulation using plant-based oil. However, food security has caused concerns in development of new bio-lubricants. In this study, treated used cooking palm oil added with Zinc Dialkyldithiophosphate and Molybdenum Disulphide nanoparticles were used as lubricant to assist the cutting of hardened martensitic stainless steel AISI420 using coated carbide tool. Surface roughness of the cut workpiece was investigated using a surface roughness tester. From the study, treated used cooking oil added with ZDDP and 0.8wt% MoS_2 nanoparticles displayed the lowest average surface roughness of workpiece with $R_a = 0.532\mu\text{m}$ and total roughness $R_z = 4.006\mu\text{m}$. This concluded that the new formulated bio-lubricant can successfully replace the readily available commercial cutting fluid as it produces a low surface roughness during cutting process.

1. Introduction

Commercially available petroleum-based lubricants are known to be harmful to the environment [1]. The improper disposal of its waste may cause severe damage to the environment. Apart from that, some health concerns arise while dealing with petroleum-based lubricants especially on handling and inhaling of its fumes during high temperature processes [2]. With these in view, many researchers have shifted the precursor for lubricant formulation to bio-based products. Vegetable oil-based lubricants were seen to be a very suitable candidate to replace petroleum-based counterpart for its high stability in high temperature and excellent lubricity characteristics. According to Rao *et al.*, vegetable oil was selected for the bio-degradability and renewability characteristics as well as the small impact it has upon the environment during disposal [3]. Farhanah *et al.*, studied the

* Corresponding author.

E-mail address: norhasrul@utm.my

<https://doi.org/10.37934/armne.14.1.17>

use of palm oil as lubricant [4], Shafi and Charoo studied the feasibility of utilizing hazelnut oil as bio-lubricant [5] while Nuri *et al.*, studied the use of corn oil to replace petroleum-based oil as bio-lubricants [6]. The addition of various additives into the different type of oil has successfully displayed the superiority of vegetable-based lubricant as a substitute to petroleum-based lubricant. However, due to food security concerns, it is not advisable for lubricant to be formulated using food-based oil [7]. Some concerns arise pertaining to food availability if the food-based vegetable oil is being used as precursor for machinery lubricant.

Malaysia is one of the biggest palm oil producer and consumer in the world. Currently the usage of palm oil in Malaysia has produced up to 50,000 tons of waste cooking palm oil [8]. This is such a huge amount of waste that could be use and utilize to be the precursor for a bio-lubricant formulation. However, prior to be use as a bio-lubricant, these used cooking palm oil shall be treated as to remove unwanted impurities such as solid particles, free fatty acids and free water diluted in the oil from frying processes [9,10].

The machining industry is an important and strategic industry for manufacturing sectors. Investigations have been carried out on machining processes by varying the cutting conditions and measuring the various machinability responses [11]. One of the main problems in conventional cutting processes is the high temperature caused by the friction between the workpiece and the cutting tool, which leads to a decrease in productivity and a breakdown in the cutting tool [12]. Since long, mineral oils have been commonly used as a base fluid in conventional cutting. However, there has been no solid evidence that treated used cooking oil can be successfully replace the use of petroleum-based lubricant. As such, this study has investigated the use of treated used cooking oil added with Zinc Dialkyldithiophosphate (ZDDP) and Molybdenum Disulphide (MoS_2) nanoparticles as bio-lubricant to assist turning of martensitic hardened stainless steel AIS420 using a coated carbide tool.

2. Methodology

2.1 Sample Preparation

Used cooking palm oil were collected from local food chain restaurants. Solid particles were removed from the used cooking palm oil and further neutralized using 2ml of 18wt% Sodium Hydroxide (NaOH) solution. Upon addition of NaOH into the waste cooking oil, the mixture was heated at 60°C for 30 minutes. The prepared samples were centrifuged at a speed of 1200 rpm for 10 minutes and then filtered for soap and solid particles removal. Zeolite 4A were used to remove free water contained in the treated used cooking oil. Zinc Dialkyldithiophosphate (ZDDP) and Molybdenum Disulphide (MoS_2) nanoparticles were purchased and used without any treatment process. ZDDP were added at a constant concentration of 2wt% while concentration of MoS_2 were varied at 0.4wt%, 0.8wt% and 1.2 wt%.

2.2 Preparation of Workpiece and Cutting Tools

Martensitic Stainless Steel AISI420 with a HRC of 50 (dimension: 50mm diameter, 90mm length) were used as workpiece. Turning of the workpiece uses the Pinacho S-90/180 lathe machine for 0.20 mm depth of cut at a moderate machining (135 m/min) medium speed and 0.20 mm/rev feed rate. The cutting tool used was coated carbide with TiAlN. The cutting of the workpiece employed a dry lubrication as well as flood lubrication at 6L/hour.

2.3 Determination of Additive Dilution

The prepared samples were tested for the additive dilution by using Spectroil Q100 Rotating Disc Electrode Atomic Emission Spectroscopy (RDE-AES) in accordance with ASTM D6595. The concentrations of zinc, molybdenum and phosphorus particles in the samples were determined by using RDE-AES to observe the dilution of ZDDP and MoS₂ nanoparticles into the treated used cooking palm oil.

2.4 Surface Roughness

The surface roughness of the cut workpiece was examined using a Mitutoyo SJ-310 surface roughness tester. A gaussian filter was used at $\lambda = 0.5\text{mm/s}$ and $\lambda_c = 0.25$.

3. Results

3.1 Determination of Elements

The prepared samples were tested for dilution of additives. The dilution for Zinc, Phosphorous and Molybdenum were investigated as this will ensure the effectiveness of the newly formulated bio-lubricant developed through addition of ZDDP and MoS₂ nanoparticles. The concentration of each elements observed were recorded as in Table 1.

Table 1
Concentration of Zinc, Phosphorous and Molybdenum in different bio-lubricant samples

Sample	Concentration (ppm)		
	Zinc	Phosphorous	Molybdenum
Treated used cooking oil	Not detected	17	Not detected
TCO + 0.4wt% MoS ₂	Not detected	18	1872
TCO + 0.8wt% MoS ₂	Not detected	16	3551
TCO + 1.2wt% MoS ₂	Not detected	17	5497
TCO + ZDDP + 0.4wt% MoS ₂	1404	1675	1861
TCO + ZDDP + 0.8wt% MoS ₂	1399	1660	3529
TCO + ZDDP + 1.2wt% MoS ₂	1434	1719	5476

From Table 1, it can be observed that treated used cooking oil do not contain any Zinc and Molybdenum. Zinc was also not detected for treated used cooking oil added with MoS₂ nanoparticles without ZDDP. However, it can be clearly seen that when the treated used cooking oil were added with MoS₂ nanoparticles, the concentration of Molybdenum started to increase. This clearly indicated that the Molybdenum was properly dissolved into the precursor of treated used cooking oil. On the other hand, while the treated used cooking oil were added with ZDDP and MoS₂ nanoparticles, the concentration of Zinc and Phosphorous started to increase as well as the concentration of Molybdenum. The gradual consistent increase in Molybdenum correlates with the increase in MoS₂ nanoparticles loading whereby the loading were gradually increase from 0.4wt% to 0.8wt% and 1.2wt%. The almost constant value of Zinc concentration confirms that the Zinc added to all samples were at the same concentration which is at 2.0wt%. This is a clear statement of dilution of ZDDP and MoS₂ as ZDDP were made of Zinc and Phosphorous elements while MoS₂ resulted from the combination of Molybdenum and Sulfur [13]. The similar trend was also observed by Nuri *et al.*, using RDE-AES to confirm dilution of Zinc in corn oil [6].

3.2 Surface Roughness

To investigate the effect of different concentration of Molybdenum Disulfide in the newly formulated bio-lubricant, the treated used cooking oil added with different additives were tested during cutting process of martensitic stainless steel AISI420 using a coated carbide tool. The surface roughness of the cut workpiece was investigated and the value recorded. The trend of average surface roughness, Ra and height of roughness Rz were depicted as in Figure 1.

From the data, it is evident that the workpiece cut without any lubricant applied displayed a very high Ra at $2.922\mu\text{m}$ and Rz of $13.523\mu\text{m}$. However, with the assistance of a simple lubricant, a treated used cooking oil, the average surface roughness reduced to Ra = $1.959\mu\text{m}$ and Rz = $9.909\mu\text{m}$. This clearly indicated that without any lubrication during the cutting process, the workpiece experienced a highly abrasive cutting process. This is because the cutting process without any lubricant has caused the workpiece to experience a higher friction between the workpiece and cutting tool. This increased friction between the contacting surfaces caused the workpiece to result in a higher abrasive wear which in showed through the high value of Ra and Rz. With the application of lubricant, the workpiece was being protected by a thin layer to prevent from excessive heat being generated during cutting process [14]. The lubrication applied also assisted in lowering the friction during cutting process that caused the wear to also reduce. This is clear through a reduction of Ra and Rz compared to the cutting process without any lubricant.

The addition of MoS₂ nanoparticles further reduced the value of average surface roughness and total surface roughness of the workpiece. As the treated used cooking palm oil were added with 0.4wt% MoS₂, the average surface roughness reduced to $1.366\mu\text{m}$ and total surface roughness of $8.929\mu\text{m}$. Further reduction was recorded when the treated used cooking oil were added with 0.8wt% MoS₂ nanoparticles with Ra = $1.105\mu\text{m}$ and Rz = $4.992\mu\text{m}$. The addition of MoS₂ nanoparticles into the lubricant were seemed to be lowering the surface roughness of workpiece. The addition of sufficient amount of MoS₂ nanoparticles is seen to be assisting in reducing the friction as MoS₂ nanoparticles at the desired amount can be an efficient friction modifier. The presence of MoS₂ nanoparticles supported in the sliding effect between the contacting surfaces causing the friction to be lowered hence reducing the wear within [15,16]. This is the reason for the reduction in surface roughness values when the treated used cooking oil were added with 0.4wt% and 0.8wt% of MoS₂ nanoparticles. However, when 1.2wt% of MoS₂ nanoparticles were being added into the treated used cooking palm oil, the surface roughness of the workpiece displayed a slight increase of Ra to $1.153\mu\text{m}$ and Rz to $4.429\mu\text{m}$. The excessive addition of MoS₂ nanoparticles into the treated used cooking palm oil bio-lubricant has caused the nanoparticles to excessively collide between one another and cause the friction to increase. This may be the reason of increase in surface roughness as the friction between cutting tools and workpiece increased due to the excess concentration of MoS₂ nanoparticles.

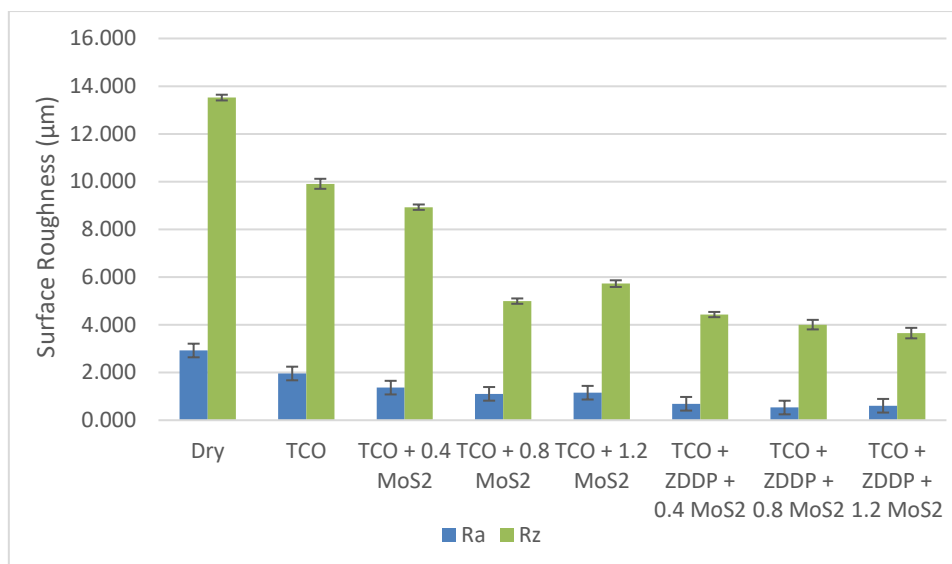


Fig. 1. Average surface roughness and total roughness of workpiece cut with different concentration of additives

As the treated used cooking oil were added with ZDDP and MoS₂ nanoparticles, the average surface roughness and total height roughness of workpiece were observed to be reducing further. The interaction between ZDDP and MoS₂ has completely given a well lubricated workpiece. The average surface roughness Ra, of the workpiece lubricated with treated used cooking palm oil with ZDDP and 0.4wt% MoS₂ nanoparticles was reduced to 0.690µm with Rz reduced to 4.429µm while addition of ZDDP and 0.8 wt% MoS₂ reduced the average surface roughness of the workpiece lower to Ra = 0.532µm and total roughness Rz = 4.006µm. ZDDP added into the lubricant as additive acted as a protective surface layer that could reduce unwanted wear from occurring [17]. The synergistic effect between ZDDP and MoS₂ nanoparticles clearly effected in lowering the wear with the optimum concentration of MoS₂ nanoparticles added was at 0.8%wt [18–20]. Trend increasing trend of average surface roughness was also observed when the treated used cooking oil was added with ZDDP and 1.2wt% MoS₂ nanoparticles. While the ZDDP added acted as an anti-wear agent to reduce wear, excess MoS₂ nanoparticles were observed to increase the collision within the lubricant causing the friction to increase hence increasing the value of average surface roughness of workpiece. The microstructure of different cutting lubricants is depicted as in Figure 2.

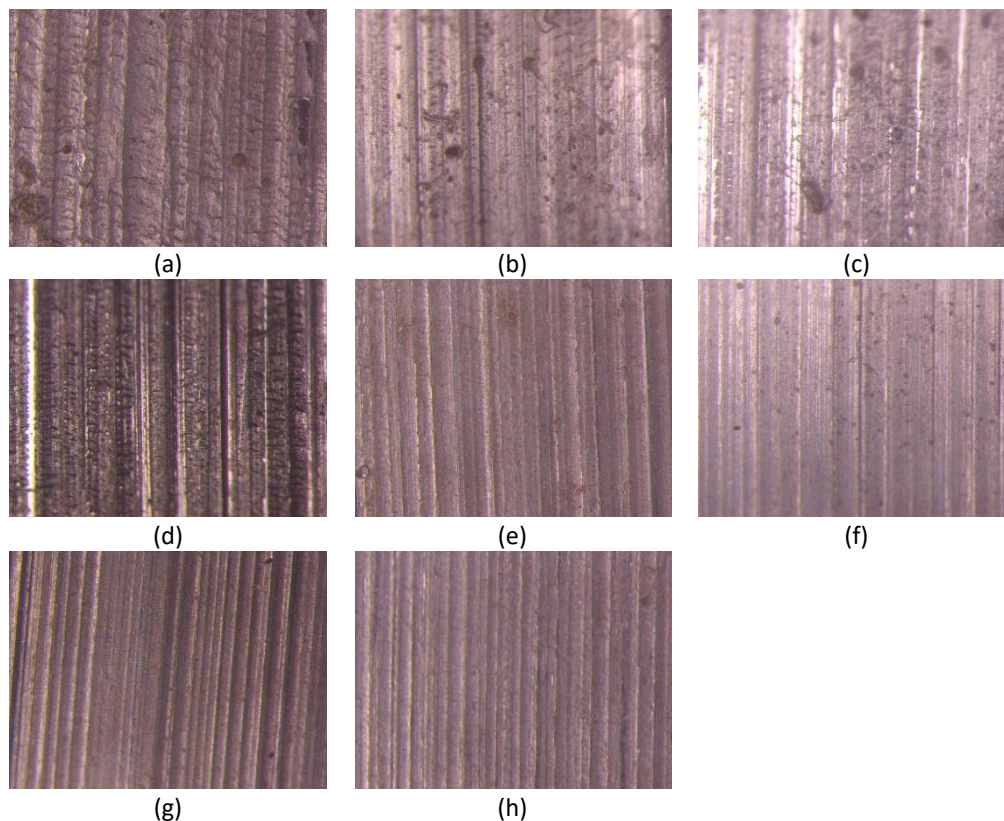


Fig. 2. Microstructures of cutting samples with different lubrication (a) Dry lubrication (b) Treated cooking oil (c) Treated cooking oil + 0.4wt% MoS₂ (d) Treated cooking oil + 0.8wt% MoS₂ (e) Treated cooking oil + 1.2wt% MoS₂ (f) Treated cooking oil + ZDDP and 0.4wt% MoS₂ (g) Treated cooking oil + ZDDP and 0.8wt% MoS₂ (h) Treated cooking oil + ZDDP and 1.2wt% MoS₂

4. Conclusion

A new formulated bio-lubricant for cutting of AISI420 martensitic stainless steel was successfully formulated through addition of ZDDP and MoS₂ nanoparticles into treated used cooking palm oil. The cutting of workpiece displayed the lowest average surface roughness Ra = 0.532μm and total roughness Rz = 4.006μm with the addition of 2wt% ZDDP and 0.8wt% MoS₂ nanoparticles. This new formulation may be the solution to treat excessive generation of waste cooking oil as well as an alternative to the use of readily available commercially petroleum-based lubricants.

Acknowledgment

The author would like to acknowledge the financial support from Ministry of Higher Education Malaysia and Universiti Teknologi Malaysia for the funding under UTM High Impact Research Grant (UTM HIR) (Q.J130000.2451.08G65)

Reference

- [1] Sneha, E., S. Rani, and Muhammed Arif. "Evaluation of lubricant properties of vegetable oils as base oil for industrial lubricant." In *IOP Conference Series: Materials Science and Engineering*, vol. 624, no. 1, p. 012022. IOP Publishing, 2019. <https://doi.org/10.1088/1757-899X/624/1/012022>
- [2] Azhari, Muhamad Azwar, Muhammad Syafi Md Sallehan, and Muhammad Naqib Nazri. "Oxidation stability comparison between zinc dialkyldithiophosphate and zinc diamyldithiocarbamate induced palm oil bio-lubricants." *Journal of Mechanical Engineering (JMEchE)* 2 (2017): 23-29.

- [3] Rao, T. V. V. L. N., Ahmad Majdi Abdul Rani, Mokhtar Awang, Masri Baharom, and Yoshimitsu Uemura. "Biolubricants with additives in Malaysia for tribological applications." *Handbook of Nanomaterials and Nanocomposites for Energy and Environmental Applications* (2020): 1-14. https://doi.org/10.1007/978-3-030-11155-7_6-1
- [4] Farhanah, A. N., S. Syahrullail, M. N. Musa, and M. Z. Bahak. "Modification of RBD palm kernel and RBD palm stearin oil with ZDDP additive addition." *Jurnal Teknologi* 74, no. 10 (2015): 121-126. <https://doi.org/10.11113/jt.v74.4842>
- [5] Shafi, W. K., & Charoo, M. S. (2021). Antiwear and extreme pressure properties of hazelnut oil blended with ZDDP. *Industrial Lubrication and Tribology*, 73(2), 297-307. <https://doi.org/10.1108/ILT-06-2020-0217>
- [6] Nuri, NR Mat, Q. N. Suffian, M. F. H. M. Saroji, and M. A. Azhari. "Addition of ZDDP in corn oil as lubricant physical property improver." In *Proceedings of Malaysian International Tribology Conference*, vol. 2015, pp. 213-214. 2015.
- [7] Yusoff, Mohd Nur Ashraf Mohd, Nurin Wahidah Mohd Zulkifli, Nazatul Liana Sukiman, Ong Hwai Chyuan, Masjuki Haji Hassan, Muhammad Harith Hasnul, Muhammad Syahir Amzar Zulkifli, Muhammad Mujtaba Abbas, and Muhammad Zulfattah Zakaria. "Sustainability of palm biodiesel in transportation: a review on biofuel standard, policy and international collaboration between Malaysia and Colombia." *Bioenergy research* 14 (2021): 43-60.
- [8] Kabir, Ibrahim, M. Yacob, and Alias Radam. "Households' awareness, attitudes and practices regarding waste cooking oil recycling in Petaling, Malaysia." *IOSR Journal of Environmental Science, Toxicology and Food Technology* 8, no. 10 (2014): 45-51. <https://doi.org/10.9790/2402-081034551>
- [9] Miskah, S., T. Aprianti, M. Agustien, Y. Utama, and M. Said. "Purification of used cooking oil using activated carbon adsorbent from durian peel." In *IOP Conference Series: Earth and Environmental Science*, vol. 396, no. 1, p. 012003. IOP Publishing, 2019. <https://doi.org/10.1088/1755-1315/396/1/012003>
- [10] Szabo, Zoltan, Tamas Marosvölgyi, Eva Szabo, Viktor Koczka, Zsafia Verzar, Maria Figler, and Tamas Decsi. "Effects of repeated heating on fatty acid composition of plant-based cooking oils." *Foods* 11, no. 2 (2022): 192. <https://doi.org/10.3390/foods11020192>
- [11] Elmunafi, Mohamed Handawi Saad, Denni Kurniawan, and M. Y. Noordin. "Use of castor oil as cutting fluid in machining of hardened stainless steel with minimum quantity of lubricant." *Procedia Cirp* 26 (2015): 408-411. <https://doi.org/10.1016/j.procir.2015.03.001>
- [12] Elmunafi, Mohamed Handawi Saad, M. Y. Noordin, and Denni Kurniawan. "Tool life of coated carbide cutting tool when turning hardened stainless steel under minimum quantity lubricant using castor oil." *Procedia Manufacturing* 2 (2015): 563-567. <https://doi.org/10.1016/j.promfg.2015.07.097>
- [13] Yamamoto, Yuji, and Seigo Gondo. "Friction and wear characteristics of molybdenum dithiocarbamate and molybdenum dithiophosphate." *Tribology Transactions* 32, no. 2 (1989): 251-257. <https://doi.org/10.1080/10402008908981886>
- [14] Noordin, Mohd Yusof, V. C. Venkatesh, S. Sharif, S. Elting, and A. Abdullah. "Application of response surface methodology in describing the performance of coated carbide tools when turning AISI 1045 steel." *Journal of materials processing technology* 145, no. 1 (2004): 46-58. [https://doi.org/10.1016/S0924-0136\(03\)00861-6](https://doi.org/10.1016/S0924-0136(03)00861-6)
- [15] Parenago, O. P., V. N. Bakunin, G. N. Kuz'Mina, A. Yu Suslov, and L. M. Vedeneeva. "Molybdenum sulfide nanoparticles as new-type additives to hydrocarbon lubricants." In *Doklady Chemistry*, vol. 383, pp. 86-88. Kluwer Academic Publishers-Plenum Publishers, 2002. <https://doi.org/10.1023/A:1014791509751>
- [16] Unnikrishnan, R., M. C. Jain, A. K. Harinarayan, and A. K. Mehta. "Additive-additive interaction: an XPS study of the effect of ZDDP on the AW/EP characteristics of molybdenum based additives." *Wear* 252, no. 3-4 (2002): 240-249. [https://doi.org/10.1016/S0043-1648\(01\)00865-1](https://doi.org/10.1016/S0043-1648(01)00865-1)
- [17] Azhari, Muhamad Azwar, M. F. H. M. Saroji, and M. A. Latif. "Comparison of tribological properties between canola oil-t-ZDDP and." *J Eng Appl Sci* 100 (2016): 2126-2129.
- [18] Parenago, O. P., G. N. Kuz'mina, and T. A. Zaimovskaya. "Sulfur-containing molybdenum compounds as high-performance lubricant additives." *Petroleum Chemistry* 57 (2017): 631-642. <https://doi.org/10.1134/S0965544117080102>
- [19] Ye, Jiping, Makoto Kano, and Yoshiteru Yasuda. "Evaluation of local mechanical properties in depth in MoDTC/ZDDP and ZDDP tribochemical reacted films using nanoindentation." *Tribology Letters* 13 (2002): 41-47.
- [20] Azhari, Muhamad Azwar, Lokman Hakim Mat, and M. F. H. M. Saroji. "A Review on Addition of Molybdenum Compounds into Zinc Induced." *Journal of Engineering and Applied Sciences* 100, no. 9 (2016): 2050-2053.