




Journal of Research in Nanoscience and Nanotechnology

Journal homepage:
www.akademiabaru.com/jrnn.html
ISSN: 2773-6180

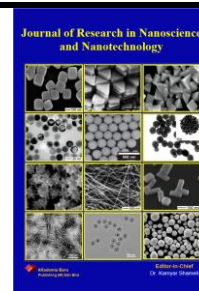

Photocatalytic Degradation with Green Synthesized Metal Oxide Nanoparticles – A Mini Review

Eleen Dayana Mohamed Isa ¹, Kamyar Shameli ^{1,*}, Nurfatehah Wahyuny Che Jusoh ^{1,2}, Siti Nur Amalina Mohamad Sukri ¹ and Nur' Afini Ismail ¹

Department of Chemical and Environmental Engineering, Malaysia-Japan International Institute of Technology, Universiti Teknologi Malaysia, Jalan Sultan Yahya Petra, 54100 Kuala Lumpur Malaysia ¹

Advanced Materials Research Group, Center of Hydrogen Energy, Universiti Teknologi Malaysia, 54100, Kuala Lumpur, Malaysia. ²

* Correspondence: kamyarshameli@gmail.com; Tel.: +6017 344 3492

<https://doi.org/10.37934/jrnn.2.1.7081>

ABSTRACT

Water pollution is one of the major problems faced by mankind worldwide. With the increase of populations and urbanization, the natural water resources are under great threat due to the release of untreated effluent. An alternative treatment method, photocatalysis, emerged as a promising solution. Photocatalysis process utilizes photosensitive catalyst to degrade the pollutant and one of the most common catalyst being used is metal oxide. To increase the photocatalytic activity, nanosized metal oxide being used instead of its bulk form. In these recent years, metal oxide nanoparticles production has been shifted towards a more environmentally friendly process which is also commonly known as green synthesis. In this review, we discussed on the photocatalytic process and production via green synthesis of common metal oxide nanoparticles being used as photocatalyst.

Keywords: Metal oxide, nanoparticles, green synthesis, photocatalysis

ch 2021

Revised: 13 March 2021

Received: 29 March 2021

Revised: 23 April 2021

Accepted: 12 May 2021

Publ

1. Introduction

Water pollution is one of the major issues faced by mankind worldwide. Natural resources are under great threat with the increase of populations and urbanization. Statistic show that about 1.2 billion people unable to access safe drinking water and millions died due to diseases cause by unsafe water [1]. Major contributor to the pollution of natural waters is the effluent from various industries. According to the World Bank's estimation, textile dyeing and treatment effluent cause about 20 % of

water pollution [2]. The industries wastewater being released contained various toxic compounds which can cause harmful effect to both human and aquatic life [3, 4].

In a conventional wastewater treatment, biological process followed by chemical coagulation is employed. Although this treatment unit's processes are effective in various pollutants, it is high in cost as it requires specific equipment and high energy. Furthermore, generation of large amount of by-product lead to problem of safe disposal [4, 5]. Due to these issues, the focus of textile wastewater treatment has been shifted to advanced oxidation processes (AOPs). This process involves the generation and the use of the hydroxyl radical as strong oxidant to destroy the compounds until all the constituents degraded or mineralized to carbon dioxide and water [5, 6]. The most common AOPs process being research is photocatalysis. Photocatalysis utilizes semiconductor materials such as titanium dioxide (TiO_2), zinc oxide (ZnO) and iron oxide gain much interest in treatment of wastewater due to its safe and detoxification nature to the environment [7].

Nanotechnology has garnered a lot of attention around the world across many fields. It is defined as a field of research that involved in the development of very small materials which is within nanometer range [8]. Nanomaterials are unique as they display different properties compared to their bulk counterpart. Due to their small size, they have a greater relative surface area which resulted to enhance properties [9, 10]. To obtain nanomaterials, there are two main approaches which are "top-down" and "bottom-up" approach. In "top-down" approach, it involves breakage of large material to nanomaterials. However, this method generate particles with wide size distribution and variation of morphologies [11]. "Bottom-up" approach is much more common in nanomaterials synthesis and it involves the growing of nanoparticles from single atom [8]. This approach resulted in better nanomaterials in terms of shape and size which is useful in targeted applications. In these recent years, the synthesis process has been more focus towards green synthesis [12]. In general, green synthesis makes use of environmentally friendly, non-toxic and safe reagent. The overall cost of synthesis process reduced because no additional chemical is needed. Furthermore, the overall experimental process is relatively mild which can save the energy. Hence this mini review focused on the photocatalytic degradation of pollutants using green synthesized metal oxide nanoparticles.

2. Photocatalytic process

Advanced oxidation processes (AOPs) is one of the emerging techniques in wastewater treatment and this is due to previous reports of the success of almost complete pollutants' degradation [13, 14]. AOPs able to degrade the pollutants through the production of reactive oxygen species such as hydroxyl ($\cdot\text{OH}$) and superoxide ($\cdot\text{O}_2^-$) radicals and generation of these radical species can proceed to several pathways. The four most common and well-known pathways are photolysis, ozonation, Fenton process and photocatalysis. Photolysis and ozonation defined as methods that use hydrogen peroxide together with ultraviolet and ozone to generate radical species respectively. Fenton process is currently being used as part of wastewater treatment and this process involve the usage of hydrogen peroxide with ferrous ion as catalyst. The last pathway is photocatalysis and generation of radical species is through utilization of light absorbing materials such as semiconductor materials [15, 16]. Among these four methods, photocatalysis method has been gaining preference over the other method due to the nature of photocatalysis which utilizes renewable solar energy and does not rely on the usage of chemical. Therefore, photocatalysis is considered as green and sustainable process.

Photocatalysis mechanism for pollutant degradation can proceed through two pathways which are indirect and direct mechanism with indirect mechanism being the most common. In the indirect reaction process, it begins with photoexcitation. Through irradiation of light, the semiconductor will be activated. The photon energy from light source will excite the electron from valence band (VB) to

the conduction band (CB) and this led to generation of hole (h^+) in VB and photogenerated electron (e^-) in CB. The e^- in CB will react with dissolve oxygen to form O_2^- radical and this radical will further react with water to form $\cdot OH$ radicals. In the VB, the h^+ will react with water to form $\cdot OH$ radicals. $\cdot OH$ radicals is the most crucial as it is the main radical that involve in the degradation of pollutantss [16, 17]. The schematic representation of photocatalytic pollutant degradation is shown in Figure 1 and the reaction of pollutant degradation can be expressed as follow:

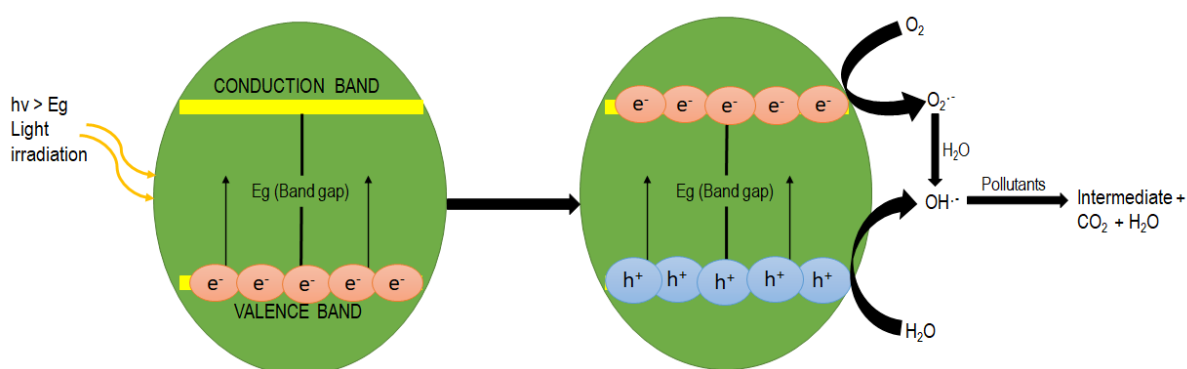





Figure 1. Schematic representation of photocatalytic degradation process.

3. Green synthesis metal oxide nanoparticles

Recent researches on synthesis of nanoparticles have been focusing on green chemistry pathway. This pathway utilizes biological entities such as plants, microorganism and carbohydrate in the production of nanoparticles [18, 19]. Previous researches showed that green synthesized nanomaterials exhibited better size and morphology. Furthermore, green synthesis process poses many advantages such as environmentally friendly, simple, easy, economical and mild synthesis process [20]. In this section, we will be focusing on the green synthesized metal oxide nanoparticles such as titanium dioxide nanoparticles (TiO_2 NPs), zinc oxide nanoparticles (ZnO NPs) and iron oxide nanoparticles (IONPs) for the application of photocatalytic degradation of pollutants. Table 1 shows the green synthesized metal oxide nanoparticles with the respective green agent and their application towards photocatalytic degradation.

1 Table 1: Green synthesized metal oxide nanoparticles and their application towards photocatalytic degradation

| Metal oxide nanoparticles | Biomaterial | Size and morphology | and Pollutants | Photodegradation | Light irradiation | References |
|---------------------------|--|---------------------------------|--|--|-------------------|------------|
| TiO ₂ | Aloe vera leaves extract | Flake like 96 nm | Rhodamine B | 58 % (50 min) | Visible | [21] |
| | Mangrove extract | Deformed Spherical 40 nm | Reactive blue 19 Red 76 | ~15 % (120 min) ~15 % (120 min) | Visible | [22] |
| | <i>Calotropis gigantea</i> leaf extract | Spherical 42 nm | Metformin | 97 % (240 min) | Visible | [23] |
| | <i>Aegle marmelos</i> leaf extract | Spherical 150 nm | Ornidazole | 66 % (300 min) | UV | [24] |
| | <i>Monsonia burkeana</i> plant extract | Spherical 2 – 18 nm | Methylene blue | 86 % (180 min) | UV | [25] |
| | <i>Lagenaria siceraria</i> leaf extract | Irregular sphere 10 – 14 nm | Reactive green 19 | 99 % (60 min) | UV | [26] |
| | <i>Citrus aurantium</i> fruit peel extract | Spherical 34 nm | Methylene blue | 91 % (150 min) | UV | [27] |
| | <i>Deinbollia pinnata</i> leaves extract | Semi-spherical 33-48 nm | Methyl orange | 99 % (150 min) | UV | [28] |
| | <i>Acacia catechu</i> extract | Spherical hexagonal 18 nm | and Rhodamine B Rose bengal | 99 % (120 min) 97 % (120 min) | Visible | [29] |
| | <i>Salvia officinalis</i> leaves extract | Spherical 50 – 120 nm | Reactive black 5 Reactive blue 19 Brilliant blue R | 69 % (60 min) 74 % (60 min) 79 % (60 min) | UV | [30] |

| | | | | | | |
|-----|--|------------------------------------|--|---|---------|------|
| ZnO | <i>Averrhoë carrambola</i> fruit extract | Flake like 20 nm | Congo red | 93 % (180 min) | UV | [31] |
| | <i>Abelmoschus esculentus</i> mucilage | Spheres and rod like 29 – 70 nm | Methylene Blue Rhodamine B | 95 % (60 min) 100 % (50 min) | UV | [32] |
| | Eucalyptus leaf extract | Agglomerated particles | Malachite green | 90 % (60 min) | UV | [33] |
| | <i>Cynara scolymus</i> leave extract | Spherical 66 nm | Methyl violet Malachite green | 94 % (120 min) 90 % (120 min) | UV | [34] |
| | <i>Cyanometra ramiflora</i> leaves extract | Nanoflowers | Rhodamine B | 98 % (200 min) | Visible | [35] |
| | <i>Punica granatum</i> leaves extract | Spherical 10 – 30 nm | Coomassie brilliant blue R-250 | ~89 % (180 min) | Visible | [36] |
| | <i>Hydnocarpus alpina</i> extract | Spherical 39 nm | Methylene blue | 96 % (30 min) | UV | [37] |
| | Longan seed extract | Hexagonal 10 – 100 nm | Methylene blue Malachite green Methyl orang Orange II | ~100 % (180 min) ~85 % (180 min) ~55 % (180 min) ~80 % (180 min) | Visible | [38] |

| | | | | | | |
|-------|---|---|------------------------------|--|---------|------|
| | <i>Leucaena leucocephala</i> leaves extract | Spherical 50 – 200 nm | Crystal violet | ~99 % (90 min) | UV | [39] |
| | <i>Mussaenda frondosa</i> leaves, stems and callus extracts | Spongy, spherical and porous agglomerated nanoparticles | Methylene blue | 30 – 90 % (120 min) | UV | [40] |
| | <i>Ulva lactuca</i> seaweed extract | Agglomerated sponge like 10 – 50 nm | Methylene blue | 90 % (120 min) | Visible | [41] |
| | Pullulan | Spherical and hexagonal 28 – 127 nm | Methyl orange Rhodamine B | ~99 % (60 min) ~99 % (60 min) | UV | [42] |
| IONPs | <i>Aegle marmelos</i> extract | Agglomerated particles | Brilliant green | 96 % (90 min) | UV | [43] |
| | <i>Tamarix aphylla</i> extract | Spherical | Methylene blue | 100 % (60 min) | Visible | [44] |
| | <i>Wedelia urticifolia</i> DC. Leaf extract | Nanorod 15 – 70 nm | Methylene blue | 98 % (360 min) | Visible | [45] |
| | <i>Withania coagulans</i> extract | Nanorods 16 nm | Sarafanin dye | ~70% (180 min) | Visible | [46] |
| | <i>Carica papaya</i> leaves extract | Agglomerated particles 22 nm | Remazol yellow RR dye | 77 % (360 min) | Visible | [47] |
| | <i>Ruellia tuberosa</i> leaves extract | Hexagonal nanorods 53 nm | Crystal violet | 80 % (150 min) | Visible | [48] |
| | <i>Psidium guavaja</i> and <i>Moringa oleifera</i> leaves extract | Spherical and non-uniformed rod 1 nm | Methylene blue | ~20 % (60 min) | Visible | [49] |

| | | | | | |
|---|------------------------------|------------------------------|-------------------|---------|------|
| <i>Rhizophora mucronata</i> leaves extract | Agglomerated particles | Phenol red Crystal violet | 83 % 95 % | Visible | [50] |
| <i>Spiny amaranth</i> leaves extract | Spherical | Naphthalene | 97 % (150 min) | UV | [51] |
| Pomogranate seeds extract | Semi-spherical 25 – 55 nm | Reactive blue | 95 % (56 min) | UV | [52] |

3.1. Titanium dioxide nanoparticles

Titanium dioxide nanoparticles (TiO₂ NPs) is one of the most popular photocatalyst being used. This is due to their favorable properties such as non-toxic, low-cost, good photosensitivity, photocatalytic stability and abundant availability. It has the band gap value of 3.2 eV for anatase and 3.03 eV for rutile phase [53]. Sonker and co-workers reported on fabrication of TiO₂ NPs with nanosheet morphology using aloe vera leaves extract. The synthesized sample was able to degrade 58 % of Rhodamine B dye in 50 minutes under visible light irradiation [21]. In another work, TiO₂ NPs was successfully produced with *Salvia officinalis* leaves extract. The produced sample exhibited spherical morphology with particle size ranging from 50 – 120 nm. This sample managed to degrade 3 azo dyes, Reactive Black 5, Reactive Blue 19 and Brilliant Blue R with degradation percentage of 69, 74 and 79 % respectively [30].

3.2. Zinc oxide nanoparticles

Zinc oxide nanoparticles (ZnO NPs) has emerged as a promising candidate for photocatalytic degradation of dyes. ZnO can be found in nature within the earth crust in the form of mineral zincite but typically ZnO is obtained through synthesis [54]. ZnO is a n-type semiconductor which has a broad direct band gap width (3.37 eV), large excitation binding energy (60 meV) and absorb larger fraction of the UV spectrum. It has three crystal structure which are rocksalt, wurtzite and cubic (zinc blend) and among these three, wurtzite structure has the highest thermodynamic [55, 59]. Varadavenkatesan and colleagues reported on the production of ZnO NPs with nanoflowers morphology using the leaves extract of *Cyanometra ramiflora*. The synthesized sample managed to degrade Rhodamine B dye up to 98 % in 200 minutes [35]. Our previous work reported on the production of ZnO NPs using biopolymer, pullulan. The dyes Rhodamine B and Methyl orange were successfully degraded in 60 minutes under UV irradiation [42]

3.3 Iron oxide nanoparticles

Iron oxide is a transition metal oxide. It has three crystalline structure such as hematite (α -Fe₂O₃), magnetite (Fe₃O₄) and maghemite (γ -Fe₂O₃). Among all these crystal structures, hematite is most stable and most commonly applied as photocatalyst [53-57]. However, in this review, we referred any form of crystal structure as iron oxide nanoparticles (IONPs). Rather and co-workers reported on the synthesis of IONPs using *Wedelia urticifolia* DC. Leaf extract with nanorods morphology. The sample managed to degrade methylene blue dye up to 98 % in 360 minutes under visible light irradiation [45]. Another work reported on the production of IONPs using the leaves extract of spinny amaranth [58-59]. The synthesized sample was then tested towards photodegradation of naphthalene where degradation efficiency of 97 % was obtained within 150 minutes under UV irradiation [51].

4. Conclusions

In conclusion, there are various metal oxides nanoparticles that can be used for photocatalytic degradation applications with the most common being TiO₂ NPs, ZnO NPs and IONPs. Furthermore, the type of pollutants that can be degraded is no longer limited to dyes only but also extend to other organic pollutants such as pharmaceutical products and others. This review discovers that even green synthesized metal oxide nanoparticles have the capability to photodegrade the pollutants which is a promising outcome. However, this review only focused three types of metal oxide nanoparticles and only on singular state.

Funding

This research was funded by Takasago Thermal Engineering Co. Ltd. grant (#4B422) from the research management center (RMC) of Universiti Teknologi Malaysia (UTM) and Malaysia-Japan International Institute of Technology (MJIT).

Acknowledgement

The authors wish to acknowledge the members of Chemical Energy Conversions and Applications (ChECA) Research Laboratory, Department of Environment and Green Technology and the members from Centre of Hydrogen, University Technology Malaysia, Kuala Lumpur, Malaysia.

References

1. P. Ahuja, S. K. Ujjain, R. Kanojia, and P. Attri, Transition Metal Oxides and Their Composites for Photocatalytic Dye Degradation, *Journal of Composites Science*, 2021, 5.(3), [doi: 10.3390/jcs5030082](https://doi.org/10.3390/jcs5030082).
2. S. H. S. Chan, T. Yeong Wu, J. C. Juan, and C. Y. Teh, Recent developments of metal oxide semiconductors as photocatalysts in advanced oxidation processes (AOPs) for treatment of dye wastewater, *J. Chem. Technol. Biotechnol.*, 2011, 86.(9), pp. 1130-1158, doi: <https://doi.org/10.1002/jctb.2636>.
3. A. R. Khataee and M. B. Kasiri, Photocatalytic degradation of organic dyes in the presence of nanostructured titanium dioxide: Influence of the chemical structure of dyes, *J. Mol. Catal. A: Chem.*, 2010, 328.(1-2), pp. 8-26, [doi: 10.1016/j.molcata.2010.05.023](https://doi.org/10.1016/j.molcata.2010.05.023).
4. O. Sahu and N. Singh, "Significance of bioadsorption process on textile industry wastewater," in *The Impact and Prospects of Green Chemistry for Textile Technology*, 2019, pp. 367-416.
5. V. K. Saharan, D. V. Pinjari, P. R. Gogate, and A. B. Pandit, "Advanced Oxidation Technologies for Wastewater Treatment," in *Industrial Wastewater Treatment, Recycling and Reuse*, 2014, pp. 141-191.
6. Y. Deng and R. Zhao, Advanced Oxidation Processes (AOPs) in Wastewater Treatment, *Current Pollution Reports*, 2015, 1.(3), pp. 167-176, [doi: 10.1007/s40726-015-0015-z](https://doi.org/10.1007/s40726-015-0015-z).
7. R. Wahab, I. H. Hwang, Y.-S. Kim, and H.-S. Shin, Photocatalytic activity of zinc oxide micro-flowers synthesized via solution method, *Chem. Eng. J.*, 2011/03/15/ 2011, 168.(1), pp. 359-366, doi: <https://doi.org/10.1016/j.cej.2011.01.038>.
8. J. Virkutyte and R. S. Varma, "Green Synthesis of Nanomaterials: Environmental Aspects," in *Sustainable Nanotechnology and the Environment: Advances and Achievements*, (ACS Symposium Series, 2013, pp. 11-39.
9. M. Shah, D. Fawcett, S. Sharma, S. K. Tripathy, and G. E. J. Poinern, Green Synthesis of Metallic Nanoparticles via Biological Entities, *Materials (Basel)*, Oct 29 2015, 8.(11), pp. 7278-7308, [doi: 10.3390/ma8115377](https://doi.org/10.3390/ma8115377).
10. A. P. Nikalje, Nanotechnology and its Applications in Medicine, *Medicinal Chemistry*, 2015, 5.(2), pp. 81-89, [doi: 10.4172/2161-0444.1000247](https://doi.org/10.4172/2161-0444.1000247).
11. G. Salas, R. Costo, and M. d. P. Morales, "Chapter 2 - Synthesis of Inorganic Nanoparticles," in *Frontiers of Nanoscience*, vol. 4, J. M. de la Fuente and V. Grazu Eds.: Elsevier, 2012, pp. 35-79.
12. K. Parveen, V. Banse, and L. Ledwani, "Green synthesis of nanoparticles: Their advantages and disadvantages," 2016.
13. M. A. Rauf and S. S. Ashraf, Fundamental principles and application of heterogeneous photocatalytic degradation of dyes in solution, *Chem. Eng. J.*, 2009, 151.(1-3), pp. 10-18, [doi: 10.1016/j.cej.2009.02.026](https://doi.org/10.1016/j.cej.2009.02.026).
14. Z. Carmen and S. Daniela, "Textile Organic Dyes – Characteristics, Polluting Effects and Separation/Elimination Procedures from Industrial Effluents – A Critical Overview," in *Organic Pollutants Ten Years After the Stockholm Convention*, T. Puzyn and A. Mostrag-Szlichtyng Eds. Rijeka: IntechOpen, 2012, ch. 3.
15. C. Byrne, G. Subramanian, and S. C. Pillai, Recent advances in photocatalysis for environmental applications, *J. Environ. Chem. Eng.*, 2018, 6.(3), pp. 3531-3555, [doi: 10.1016/j.jece.2017.07.080](https://doi.org/10.1016/j.jece.2017.07.080).

16. A. Baruah, V. Chaudhary, R. Malik, and V. K. Tomer, "Nanotechnology Based Solutions for Wastewater Treatment," in *Nanotechnology in Water and Wastewater Treatment*, 2019, pp. 337-368.
17. A. Ajmal, I. Majeed, R. N. Malik, H. Idriss, and M. A. Nadeem, Principles and mechanisms of photocatalytic dye degradation on TiO₂ based photocatalysts: a comparative overview, *RSC Adv.*, 2014, 4.(70), pp. 37003-37026, doi: [10.1039/c4ra06658h](https://doi.org/10.1039/c4ra06658h).
18. D. Fawcett, J. J. Verduin, M. Shah, S. B. Sharma, and G. E. J. Poinern, A Review of Current Research into the Biogenic Synthesis of Metal and Metal Oxide Nanoparticles via Marine Algae and Seagrasses, *J. Nanosci.*, 2017, 2017.(pp. 1-15, doi: [10.1155/2017/8013850](https://doi.org/10.1155/2017/8013850)).
19. A. K. Mittal, Y. Chisti, and U. C. Banerjee, Synthesis of metallic nanoparticles using plant extracts, *Biotechnol. Adv.*, Mar-Apr 2013, 31.(2), pp. 346-56, doi: [10.1016/j.biotechadv.2013.01.003](https://doi.org/10.1016/j.biotechadv.2013.01.003).
20. E. D. Mohamed Isa, K. Shameli, N. W. Che Jusoh, S. N. A. Mohamad Sukri, and N. A. Ismail, Variation of Green Synthesis Techniques in Fabrication of Zinc Oxide Nanoparticles – A Mini Review, *IOP Conf. Ser., Mater. Sci. Eng.*, 2021, 1051.(1), doi: [10.1088/1757-899x/1051/1/012079](https://doi.org/10.1088/1757-899x/1051/1/012079).
21. R. K. Sonker, G. Hitkari, S. R. Sabhajeet, S. Sikarwar, Rahul, and S. Singh, Green synthesis of TiO₂ nanosheet by chemical method for the removal of Rhodamin B from industrial waste, *Materials Science and Engineering: B*, 2020, 258. doi: [10.1016/j.mseb.2020.114577](https://doi.org/10.1016/j.mseb.2020.114577).
22. E. T. Helmy, A. E. Nemr, E. Arafa, S. Eldafrawy, and M. Mousa, Photocatalytic degradation of textile dyeing wastewater under visible light irradiation using green synthesized mesoporous non-metal-doped TiO₂, *Bull. Mater. Sci.*, 2021, 44.(1), doi: [10.1007/s12034-020-02322-0](https://doi.org/10.1007/s12034-020-02322-0).
23. V. Prashanth, K. Priyanka, and N. Remya, Solar photocatalytic degradation of metformin by TiO₂ synthesized using *Calotropis gigantea* leaf extract, *Water Sci. Technol.*, Mar 2021, 83.(5), pp. 1072-1084, doi: [10.2166/wst.2021.040](https://doi.org/10.2166/wst.2021.040).
24. W. Ahmad, A. Singh, K. K. Jaiswal, and P. Gupta, Green Synthesis of Photocatalytic TiO₂ Nanoparticles for Potential Application in Photochemical Degradation of Ornidazole, *J. Inorg. Organomet. Polym. Mater.*, 2020, 31.(2), pp. 614-623, doi: [10.1007/s10904-020-01703-6](https://doi.org/10.1007/s10904-020-01703-6).
25. N. M. Ngoepe, M. M. Mathipa, and N. C. Hintsho-Mbita, Biosynthesis of titanium dioxide nanoparticles for the photodegradation of dyes and removal of bacteria, *Optik*, 2020, 224. doi: [10.1016/j.ijleo.2020.165728](https://doi.org/10.1016/j.ijleo.2020.165728).
26. H. Kaur, S. Kaur, S. Kumar, J. Singh, and M. Rawat, Eco-friendly Approach: Synthesis of Novel Green TiO₂ Nanoparticles for Degradation of Reactive Green 19 Dye and Replacement of Chemical Synthesized TiO₂, *JCS*, 2020, doi: [10.1007/s10876-020-01881-w](https://doi.org/10.1007/s10876-020-01881-w).
27. P. V.N, V. S, S. B, and P. P.K, Protection of neuronal cell lines, antimicrobial and photocatalytic behaviours of eco-friendly TiO₂ nanoparticles, *J. Environ. Chem. Eng.*, 2020, 8.(5), doi: [10.1016/j.jece.2020.104343](https://doi.org/10.1016/j.jece.2020.104343).
28. Y. Rufai, S. Chandren, and N. Basar, Influence of Solvents' Polarity on the Physicochemical Properties and Photocatalytic Activity of Titania Synthesized Using *Deinbollia pinnata* Leaves, *Front Chem*, 2020, 8.(p. 597980, doi: [10.3389/fchem.2020.597980](https://doi.org/10.3389/fchem.2020.597980)).
29. K. Chand *et al.*, Photocatalytic and antimicrobial activity of biosynthesized silver and titanium dioxide nanoparticles: A comparative study, *J. Mol. Liq.*, 2020, 316.(doi: [10.1016/j.molliq.2020.113821](https://doi.org/10.1016/j.molliq.2020.113821)).
30. M. Altikatoglu Yapaoz and A. Attar, *Salvia officinalis*-derived rutile TiO₂NPs: production, characterization, antibacterial evaluation and its effect on decolorization, *Materials Research Express*, 2019, 6.(5), doi: [10.1088/2053-1591/ab0690](https://doi.org/10.1088/2053-1591/ab0690).
31. S. Chakraborty, J. J. Farida, R. Simon, S. Kasthuri, and N. L. Mary, Avertroche carrambola fruit extract assisted green synthesis of zno nanoparticles for the photodegradation of congo red dye, *Surfaces and Interfaces*, 2020, 19. doi: [10.1016/j.surfin.2020.100488](https://doi.org/10.1016/j.surfin.2020.100488).
32. A. R. Prasad, J. Garvasis, S. K. Oruvil, and A. Joseph, Bio-inspired green synthesis of zinc oxide nanoparticles using *Abelmoschus esculentus* mucilage and selective degradation of cationic dye pollutants, *J. Phys. Chem. Solids*, 2019, 127.(pp. 265-274, doi: [10.1016/j.jpcs.2019.01.003](https://doi.org/10.1016/j.jpcs.2019.01.003)).
33. S. A. Devi, K. J. Singh, and K. N. Devi, A Comparative Study on the Photocatalytic Activity of Eucalyptus Leaf Assisted Green Synthesized ZnO and Chemically Synthesized ZnO towards the

- Degradation of Malachite Green Dye, *InFer*, 2020, 205.(1), pp. 38-51, doi: [10.1080/10584587.2019.1674995](https://doi.org/10.1080/10584587.2019.1674995).
34. M. Rajapriya *et al.*, Synthesis and Characterization of Zinc Oxide Nanoparticles Using *Cynara scolymus* Leaves: Enhanced Hemolytic, Antimicrobial, Antiproliferative, and Photocatalytic Activity, *JCS*, 2019, 31.(4), pp. 791-801, doi: [10.1007/s10876-019-01686-6](https://doi.org/10.1007/s10876-019-01686-6).
35. T. Varadavenkatesan, E. Lyubchik, S. Pai, A. Pugazhendhi, R. Vinayagam, and R. Selvaraj, Photocatalytic degradation of Rhodamine B by zinc oxide nanoparticles synthesized using the leaf extract of *Cyanometra ramiflora*, *J. Photochem. Photobiol. B*, Oct 2019, 199.(p. 111621, doi: [10.1016/j.jphotobiol.2019.111621](https://doi.org/10.1016/j.jphotobiol.2019.111621).
36. K. Singh, J. Singh, and M. Rawat, Green synthesis of zinc oxide nanoparticles using *Punica Granatum* leaf extract and its application towards photocatalytic degradation of Coomassie brilliant blue R-250 dye, *SN Appl. Sci.*, 2019, 1.(6), doi: [10.1007/s42452-019-0610-5](https://doi.org/10.1007/s42452-019-0610-5).
37. M. Ganesh, S. G. Lee, J. Jayaprakash, M. Mohankumar, and H. T. Jang, *Hydnocarpus alpina* Wt extract mediated green synthesis of ZnO nanoparticle and screening of its anti-microbial, free radical scavenging, and photocatalytic activity, *Biocatal. Agric. Biotechnol.*, 2019, 19. doi: [10.1016/j.bcab.2019.101129](https://doi.org/10.1016/j.bcab.2019.101129).
38. C. Chankaew, W. Tapala, K. Grudpan, and A. Rujiwatra, Microwave synthesis of ZnO nanoparticles using longan seeds biowaste and their efficiencies in photocatalytic decolorization of organic dyes, *Environ. Sci. Pollut. Res. Int.*, Jun 2019, 26.(17), pp. 17548-17554, doi: [10.1007/s11356-019-05099-w](https://doi.org/10.1007/s11356-019-05099-w).
39. K. Kanagamani, P. Muthukrishnan, K. Saravanakumar, K. Shankar, and A. Kathiresan, Photocatalytic degradation of environmental perilous gentian violet dye using *leucaena*-mediated zinc oxide nanoparticle and its anticancer activity, *Rare Metals*, Apr 2019, 38.(4), pp. 277-286, doi: [10.1007/s12598-018-1189-5](https://doi.org/10.1007/s12598-018-1189-5).
40. M. D. Jayappa *et al.*, Green synthesis of zinc oxide nanoparticles from the leaf, stem and in vitro grown callus of *Mussaenda frondosa* L.: characterization and their applications, *Appl Nanosci*, Apr 9 2020, pp. 1-18, doi: [10.1007/s13204-020-01382-2](https://doi.org/10.1007/s13204-020-01382-2).
41. R. Ishwarya *et al.*, Facile green synthesis of zinc oxide nanoparticles using *Ulva lactuca* seaweed extract and evaluation of their photocatalytic, antibiofilm and insecticidal activity, *J. Photochem. Photobiol. B*, Jan 2018, 178.(pp. 249-258, doi: [10.1016/j.jphotobiol.2017.11.006](https://doi.org/10.1016/j.jphotobiol.2017.11.006).
42. E. D. M. Isa, K. Shameli, N. W. C. Jusoh, and R. Hazan, Rapid photodecolorization of methyl orange and rhodamine B using zinc oxide nanoparticles mediated by pullulan at different calcination conditions, *Journal of Nanostructure in Chemistry*, 2020/10/10 2020, doi: [10.1007/s40097-020-00358-6](https://doi.org/10.1007/s40097-020-00358-6).
43. M. Sriramulu, Balaji, and S. Sumathi, Photo Catalytic, Antimicrobial and Antifungal Activity of Biogenic Iron Oxide Nanoparticles Synthesised Using *Aegle marmelos* Extracts, *J. Inorg. Organomet. Polym. Mater.*, 2020, 31.(4), pp. 1738-1744, doi: [10.1007/s10904-020-01812-2](https://doi.org/10.1007/s10904-020-01812-2).
44. W. Ahmad *et al.*, Eco-benign approach to synthesize spherical iron oxide nanoparticles: A new insight in photocatalytic and biomedical applications, *J. Photochem. Photobiol. B*, Apr 2020, 205.(p. 111821, doi: [10.1016/j.jphotobiol.2020.111821](https://doi.org/10.1016/j.jphotobiol.2020.111821).
45. M. Y. Rather and S. Sundarapandian, Magnetic iron oxide nanorod synthesis by *Wedelia urticifolia* (Blume) DC. leaf extract for methylene blue dye degradation, *Applied Nanoscience*, 2020, 10.(7), pp. 2219-2227, doi: [10.1007/s13204-020-01366-2](https://doi.org/10.1007/s13204-020-01366-2).
46. S. Qasim *et al.*, Green synthesis of iron oxide nanorods using *Withania coagulans* extract improved photocatalytic degradation and antimicrobial activity, *J. Photochem. Photobiol. B*, Mar 2020, 204.(p. 111784, doi: [10.1016/j.jphotobiol.2020.111784](https://doi.org/10.1016/j.jphotobiol.2020.111784).
47. M. S. H. Bhuiyan *et al.*, Green synthesis of iron oxide nanoparticle using *Carica papaya* leaf extract: application for photocatalytic degradation of remazol yellow RR dye and antibacterial activity, *Heliyon*, Aug 2020, 6.(8), p. e04603, doi: [10.1016/j.heliyon.2020.e04603](https://doi.org/10.1016/j.heliyon.2020.e04603).
48. S. Vasantharaj, S. Sathiyavimal, P. Senthilkumar, F. LewisOscar, and A. Pugazhendhi, Biosynthesis of iron oxide nanoparticles using leaf extract of *Ruellia tuberosa*: Antimicrobial properties and their applications in photocatalytic degradation, *J. Photochem. Photobiol. B*, Mar 2019, 192.(pp. 74-82, doi: [10.1016/j.jphotobiol.2018.12.025](https://doi.org/10.1016/j.jphotobiol.2018.12.025).

49. N. Madubuonu *et al.*, Biosynthesis of iron oxide nanoparticles via a composite of Psidium guavaja-Moringa oleifera and their antibacterial and photocatalytic study, J. Photochem. Photobiol. B, Oct 2019, 199.(p. 111601, doi: [10.1016/j.jphotobiol.2019.111601](https://doi.org/10.1016/j.jphotobiol.2019.111601)).
50. V. K. Nathan, P. Ammini, and J. Vijayan, Photocatalytic degradation of synthetic dyes using iron (III) oxide nanoparticles (Fe₂O₃-Nps) synthesised using Rhizophora mucronata Lam, IET Nanobiotechnol, Apr 2019, 13.(2), pp. 120-123, doi: [10.1049/iet-nbt.2018.5230](https://doi.org/10.1049/iet-nbt.2018.5230).
51. M. Harshiny, S. AiswaryaDevi, and M. Matheswaran, Spiny amaranth leaf extract mediated iron oxide nanoparticles: Biocidal photocatalytic propensity, stability, dissolubility and reusability, Biocatal. Agric. Biotechnol., 2019, 21. doi: [10.1016/j.bcab.2019.101296](https://doi.org/10.1016/j.bcab.2019.101296).
52. I. Bibi *et al.*, Green synthesis of iron oxide nanoparticles using pomegranate seeds extract and photocatalytic activity evaluation for the degradation of textile dye, Journal of Materials Research and Technology, 2019, 8.(6), pp. 6115-6124, doi: [10.1016/j.jmrt.2019.10.006](https://doi.org/10.1016/j.jmrt.2019.10.006).
53. O. Fawzi Suleiman Khasawneh and P. Palaniandy, Removal of organic pollutants from water by Fe₂O₃/TiO₂ based photocatalytic degradation: A review, Environmental Technology & Innovation, 2021, 21. doi: [10.1016/j.eti.2020.101230](https://doi.org/10.1016/j.eti.2020.101230).
54. S. N. A. Mohamad Sukri, K. Shameli, M. M. T. Wong, S. Y. Teow, J. Chew and N. A. Ismail. Cytotoxicity and antibacterial activities of plant-mediated synthesized zinc oxide (ZnO) nanoparticles using *Punica granatum* (pomegranate) fruit peels extract. J. Mol. Struct., 2019, 1189, pp. 57-65. doi: [10.1016/j.molstruc.2019.04.026](https://doi.org/10.1016/j.molstruc.2019.04.026).
55. H. Jahangirian, M. H. S. Ismail, M. J. Haron, R. Rafiee-Moghaddam, K. Shameli and S. Hosseini. Synthesis and characterization of zeolite/Fe₃O₄ nanocomposite by green quick precipitation method. Dig. J. Nanomater. Biostruct., 2013, 8.(4), pp. 1405-1413.
56. R. Khandanlou, M. Ahmad, H. R. Fard Masoumi, K. Shameli and M. Basri, Rapid adsorption of copper (II) and lead (II) by rice straw/Fe₃O₄ nanocomposite: optimization, equilibrium isotherms, and adsorption kinetics study. PloS one., 2015, 10.(3), pp. 1-19. doi: [10.1371/journal.pone.0120264](https://doi.org/10.1371/journal.pone.0120264).
57. Z. Izadiyan, K. Shameli, M. Miyake, H. Hara, S. H. Mohd Taib and E. Rasouli, Cytotoxicity assay of plant-mediated synthesized iron oxide nanoparticles using *Juglans regia* green husk extract. Arab. J. Chem., 2020, 13.(1), pp. 2011-2023. doi: [10.1016/j.arabjc.2018.02.019](https://doi.org/10.1016/j.arabjc.2018.02.019).
58. R. Khandanlou, M. Ahmad, K. Shameli and K. Kalantari, Synthesis and characterization of rice straw/Fe₃O₄ nanocomposites by a quick precipitation method. Molecules, 2013, 18.(6), 6597-6607. doi: [10.3390/molecules18066597](https://doi.org/10.3390/molecules18066597).
59. K. M. Lee, C. W. Lai, K. S. Ngai, and J. C. Juan, Recent developments of zinc oxide based photocatalyst in water treatment technology: A review, Water Res., Jan 1 2016, 88, pp. 428-448, doi: [10.1016/j.watres.2015.09.045](https://doi.org/10.1016/j.watres.2015.09.045).